

PAPER • OPEN ACCESS

Validity of perturbative methods to treat the spin–orbit interaction: application to magnetocrystalline anisotropy

To cite this article: M Blanco-Rey *et al* 2019 *New J. Phys.* **21** 073054

View the [article online](#) for updates and enhancements.

You may also like

- [Cloud Structure of Three Galactic Infrared Dark Star-forming Regions from Combining Ground- and Space-based Bolometric Observations](#)
Yuxin Lin, Hanyu Baobab Liu, James E. Dale et al.
- [REACTIONS OF COLD TRAPPED CH⁺ IONS WITH SLOW H ATOMS](#)
R. Plasil, T. Mehner, P. Dohnal et al.
- [Composition dependence of electro-mechanical properties and field induced phase transformations in \[001\]_c PIN–PMN–PT single crystals](#)
John A Gallagher, Jian Tian and Christopher S Lynch



OPEN ACCESS

RECEIVED

28 February 2019

REVISED

18 June 2019

ACCEPTED FOR PUBLICATION

9 July 2019

PUBLISHED

29 July 2019

Original content from this work may be used under the terms of the [Creative Commons Attribution 3.0 licence](#).

Any further distribution of this work must maintain attribution to the author(s) and the title of the work, journal citation and DOI.



PAPER

Validity of perturbative methods to treat the spin–orbit interaction: application to magnetocrystalline anisotropy

M Blanco-Rey^{1,2}, J I Cerdá³ and A Arnau^{1,2,4}¹ Departamento de Física de Materiales, Facultad de Química, Universidad del País Vasco UPV/EHU, Apartado 1072, E-20080, Donostia-San Sebastián, Spain² Donostia International Physics Center, Paseo Manuel de Lardizábal 4, E-20018, Donostia-San Sebastián, Spain³ Instituto de Ciencia de Materiales de Madrid, CSIC, Cantoblanco, E-28049, Madrid, Spain⁴ Centro de Física de Materiales CFM/MPC (CSIC-UPV/EHU), Paseo Manuel de Lardizábal 5, E-20018, Donostia-San Sebastián, SpainE-mail: maria.blanco@ehu.es**Keywords:** spin–orbit coupling, magnetocrystalline anisotropy, density functional theory, transition-metal alloysSupplementary material for this article is available [online](#)


Abstract

A second-order perturbation (2PT) approach to the spin–orbit interaction (SOI) is implemented within a density-functional theory framework. Its performance is examined by applying it to the calculation of the magnetocrystalline anisotropy energies (MAE) of benchmark systems, and its efficiency and accuracy are compared with the popular force theorem method. The case studies are tetragonal FeMe alloys (Me=Co, Cu, Pd, Pt, Au), as well as FeMe (Me=Co, Pt) bilayers with (111) and (100) symmetry, which cover a wide range of SOI strength and electronic band structures. The 2PT approach is found to provide a very accurate description for 3d and 4d metals and, moreover, this methodology is robust enough to predict easy axis switching under doping conditions. In all cases, the details of the bandstructure, including states far from the Fermi level, are responsible for the finally observed MAE value, sometimes overruling the effect of the SOI strength. From a technical point of view, it is confirmed that accuracy in the MAE calculations is subject to the accuracy of the Fermi level determination.

1. Introduction

In a model system of interacting magnetic moments various contributions can be identified that lead to the observation of the magnetic anisotropy, i.e. the existence of a preferential magnetization direction in the system. These terms are the classical dipole–dipole interaction, resulting in the so-called shape anisotropy, and quantum-mechanical ones with origin in the electronic spin–orbit interaction (SOI). These latter include the anisotropic exchanges, both the symmetric and antisymmetric (known as Dzyaloshinskii–Moriya interaction [1, 2]), and the magnetocrystalline anisotropy (MCA). Here, this fundamental property (MCA) is used as a probe for approximate methods to treat the SOI, but our methods are potentially valid to treat other physical properties determined by SOI, like anisotropic g-tensors or anisotropic exchange interaction [3], and Elliot–Yafet theory of spin relaxation [4].

The historical development of non-volatile memories based on the property of magnetoresistivity has been closely related to the ability of balancing out those competing contributions. The key achievement was the perpendicular magnetic anisotropy in thin film heterostructures, since the out-of-plane MCA at the interface tends to dominate the in-plane shape anisotropy. Indeed, the efficient spin orientation control in the ferromagnetic (FM) electrodes of magnetic tunnelling junctions is still a technological challenge. Additionally, the use of external magnetic fields for this purpose is evolving towards voltage control of spintronic devices [5, 6] and spin transfer torques induced by spin-polarized currents [7]. These advances motivate efficient, robust and accurate modelling of the physics of the MCA for different materials/interfaces under external stimuli, such as external fields or strain.

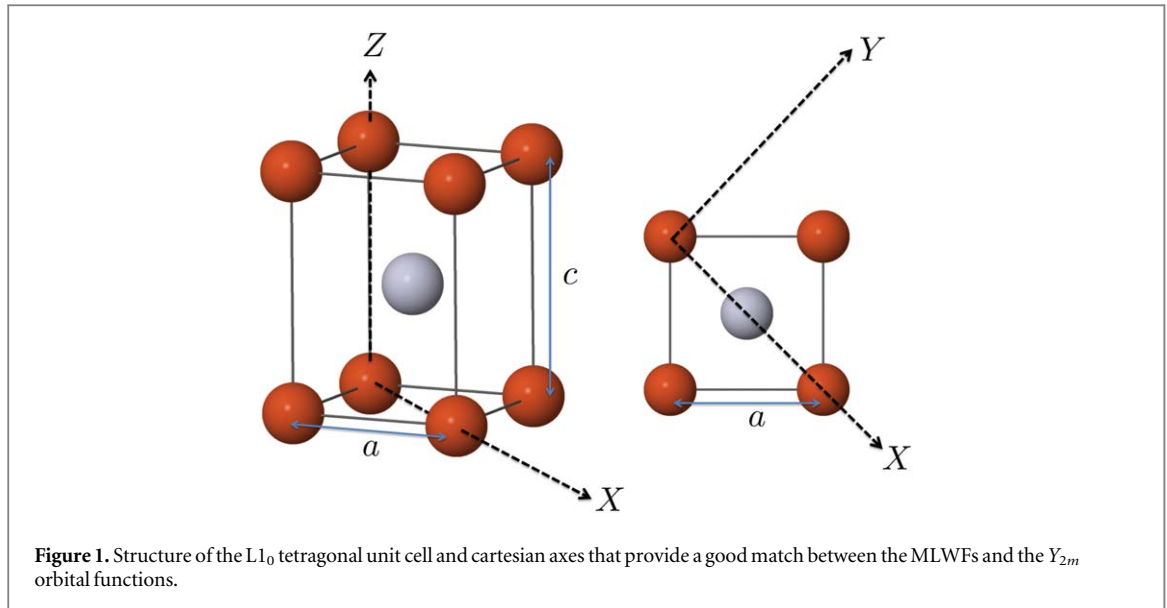

The interplay of MCA and dimensionality is considered as a promising route for the development of spintronics. Furthermore, MCA plays a central role in the magnetic properties of two-dimensional materials, since it can prevent thermal fluctuations from destroying long-range magnetic order [8]. In this context, density functional theory (DFT) calculations that include SOI constitute a powerful theoretical tool to characterize the MCA. Nonetheless, the small magnitude of the associated magnetocrystalline anisotropy energy (MAE) imposes stringent convergence to the DFT calculations at the expense of high computational demands. In practice, fully relativistic DFT calculations that include SOI are carried out by first computing self-consistently the Hamiltonian of the system including the scalar relativistic term and next adding the spin-orbit contribution. The latter may be treated self-consistently (FSC) or non-self-consistently [9, 10] within the so-called force theorem (FT) [11] to obtain the MAE. FT is often considered to produce a good estimate of the FSC MAE value for every system, at least for bulk crystals, although it has been shown to be less accurate in the case of low dimensional systems [12]. In any case, this comparison between FT and SCF calculations can only be done for relatively simple systems, because the FSC tends to be computationally too demanding. Alternatively, Green's function methods that treat SOI at the level of second-order perturbation theory (2PT) have been formulated in the literature under different flavours [13–17]. These approaches rely on the knowledge of the spin-orbit effects on atomic orbitals (AOs) [18–20], which can be quasi-analytically accounted. However, to our knowledge, the versatility of those perturbative methods has not been exploited within a DFT environment. Considering the high computational expense involved in DFT calculations that include SOI under the aforementioned techniques, it would be timely to explore the 2PT route.

In this work, we address approximate methods to treat spin-orbit effects in DFT calculations and establish their efficiency, accuracy, and applicability range using MAE values of several Fe-based alloys as benchmarks. Overall, we tackle fundamental concepts related to the magnetic anisotropy, such as the relationship between the one-electron wavefunctions used in *ab initio* or tight binding schemes with the multiplets (spin states) used in spin hamiltonian formulations [21–23]. More specifically, our aim is two-fold: (i) set the technical grounds for implementing a 2PT approach in regular DFT codes, with a detailed description of the handling of two different families of localized basis sets. Thereby, the 2PT many-body expression for the MAE is evaluated using one-electron operators and wavefunctions. (ii) Taking the FSC MAEs of the model systems as reference values, study the accuracy of the FT and 2PT approximations and their dependence on the physics of the problem. This requires to take into account careful convergence criteria.

As case studies, we choose tetragonal transition-metal alloys FeMe (Me=Co, Cu, Pd, Pt, and Au) with $L1_0$ structure (see figure 1) and we also consider thin FeMe (Me=Co, Pt) bilayers with (111) and (100) orientations. With this choice we can cover a wide range of two orders of magnitude in SOI strengths by using elements of different atomic weights and also we analyse different hybrid bands characters ($d-d$ for FeCo, FePd, and FePt, and $d-s$ for FeCu and FeAu). Additionally, the MCA of this type of alloys is well characterized and, thus, provides us with a reliable quantitative reference to compare the approximate methods considered. In fact, for solids with cubic symmetry, MCA is an effect of fourth order in the SOI strength but a tetragonal distortion can enable a second-order MCA. This idea is behind the materials used in (or proposed for) some of the aforementioned devices. For example, multiferroics allow for strain-mediated magneto-electric coupling [24, 25] and, more recently, tetragonal Heusler alloys have attracted attention for combining high MCA and half-metallicity

[26, 27]. The family of $L1_0$ alloys considered in this work is also versatile, since their structure and magnetic properties can be tailored by varying the stoichiometry, as it is the case of the strongly magnetostrictive ‘galfenol’ ($\text{Fe}_{1-x}\text{Ga}_x$) [28, 29], $\text{Fe}_{1-x}\text{Co}_x$ [30–32], and Cu–Ni films [33]. Several theoretical studies have shown that a bias voltage could significantly affect the MCA [34, 35] and, in fact, an electric-field-induced MCA switching has been realized in $\text{Fe}_{30}\text{Co}_{70}$ alloy films [36].

Our first principles calculations show that the second-order perturbative (2PT) approach to treat spin orbit interaction is very reliable for the lighter ($3d$ and $4d$) transition metals but it breaks down for heavier $5d$ elements. In general, the MAE values calculated using the force theorem (FT) agree reasonably well with the fully self-consistent calculated values also for the heavier elements, but minor quantitative discrepancies between one and other are apparent in the two-dimensional thin bilayers. The different performance of these two approximate methods is explained by their construction: while 2PT is perturbative in the spin–orbit strength, FT is perturbative in the charge density. The general character of these approaches suggests that they can be applied to any system featuring dispersive bands. Regarding the nature of the MCA in the alloys under study, we find its physical origin in the availability of empty Fe electron states, although the whole valence bandstructure contributes to its final magnitude, this latter calculated with tenths of meV precision.

The paper is organized as follows: section 2 describes the three methods used here to compute the MAE, namely FSC (section 2.1), FT (section 2.2) and, in more detail, two different implementations of a 2PT formula in DFT codes (section 2.3). Details of the DFT calculation parameters for the Fe-based alloys are presented in section 3. The results for the charge neutral and non-neutral cases are shown in sections 4.1 and 4.2, respectively. Finally, conclusions are drawn in section 5.

2. Theoretical background

The SOI Hamiltonian is generally written as a sum over one-electron operators:

$$H_{\text{SO}} = \sum_i \xi_i \mathbf{l}_i \cdot \mathbf{s}_i, \quad (1)$$

where $\mathbf{l}_i$ and $\mathbf{s}_i$ are the orbital and spin momentum operators, respectively, acting on the i th electron in the system and ξ_i accounts for the SOI strength. In practice, as most of the relevant electronic and magnetic properties of solids derived from SOI originate from valence electrons, only outer-shell and semi-core electrons are considered in our first principles calculations. Since ξ_i is proportional to the radial derivative of the potential, it increases with the atomic number. Furthermore, it is often a good approximation to take the same value for all the electrons within the same l -shell.

In the next subsections we describe the three methods considered in this work to evaluate the MAEs from first-principles, all of them including SOI at different levels of approximation. In particular, we will examine under which conditions a second-order perturbative approach, where ξ_i acts as the perturbation constant, breaks down.

2.1. Self-consistent MAE (FSC)

Our reference *ab initio* MAE value is obtained by subtracting the total energies E_{tot} between two fully-relativistic self-consistent calculations, which include SOI, for two different orientations of the magnetization,

$$\text{MAE} = E_{\text{tot}}^x - E_{\text{tot}}^z, \quad (2)$$

where the spins are aligned along the OX and OZ directions shown in the $L1_0$ unit cell model of figure 1. The main shortcoming of this method is its computational cost, since equation (2) implies subtracting two large numbers, which requires demanding convergence criteria. In fact, the obtention of well-converged MAEs from equation (2) is crucial in this work (see details in the next section), since they are used as a benchmark for the approximations described in the next subsections.

2.2. Non-self-consistent MAE based in the FT

A scalar relativistic ground state (GS) is converged in a spin-polarized calculation without SOI. The so-obtained charge density is used to initialize a fully-relativistic calculation (i.e. non-collinear) by turning it into a block-diagonal charge density matrix. Then, the spin–orbit H_{SO} term calculated for a given magnetization axis is added to the scalar-relativistic hamiltonian H_0 and new eigenvalues are calculated by diagonalization without further self-consistent cycles. We denote the resulting total energy change $\Delta E_{\text{tot}}^{x,z}$ and the corresponding charge density change $\Delta \rho^{x,z}$. The MAE is approximated as the difference in the band energies, $E_{\text{band}}^{x,z}$, between the two orientations of the magnetization, bearing in mind that the Fermi levels are in general different for the two orientations, as they are computed independently,

$$\text{MAE} \simeq \Delta E_{\text{tot}}^x - \Delta E_{\text{tot}}^z \simeq E_{\text{band}}^x - E_{\text{band}}^z = \sum_k \sum_n^{N_b} [f^x(\epsilon_{kn}^x) \epsilon_{kn}^x - f^z(\epsilon_{kn}^z) \epsilon_{kn}^z]. \quad (3)$$

Here, the sum runs over one-electron eigenvalues $\epsilon_{kn}^{x,z}$, calculated with the spins aligned along the OX and OZ directions, respectively, and integrated over the entire first Brillouin Zone (1BZ). N_b bands are considered (index n) and a discrete grid of N_k points (index k) is used to sample the 1BZ. $f^{x,z}$ are the Fermi–Dirac distribution functions, which depend on the magnetization axes through the Fermi energy, while the finite electronic temperature kT acts as a smearing parameter. The approximation is based on the fact that ΔE_{tot}^x and ΔE_{tot}^z are correct to order $(\Delta\rho^x)^2$ and $(\Delta\rho^z)^2$, respectively. The method is thus sometimes called ‘second variation’ [10] or ‘force theorem’ [9, 11]. Equation (3) is correct to order $\Delta\rho^{x,z}$ while the $(\Delta\rho^{x,z})^2$ -order corrections have a small effect, since there are cancellations from the two magnetization directions [9]. If one further assumes that the self-consistency cycles introduce negligible modifications in the charge density matrix and in the exchange and correlation potential, then equations (2) and (3) should provide very similar MAE values, although with a considerable reduction in the computational cost in the latter case.

2.3. Second-order perturbative MAE (2PT)

A widely used alternative approximation treats the SOI as a second-order perturbation (2PT) to the many-body GS, $|\Psi^{(0)}\rangle$. The general expression for the 2PT energy correction is

$$\Delta E_{\text{SO}}^{(2)} = \sum_{i \neq 0} \frac{\langle \Psi^{(0)} | H_{\text{SO}} | \Psi^{(i)} \rangle \langle \Psi^{(i)} | H_{\text{SO}} | \Psi^{(0)} \rangle}{E_0 - E_i}, \quad (4)$$

where the sum runs over excited states. In a many-body language the GS $|\Psi^{(0)}\rangle$ is formed as a Slater determinant by occupation of the lowest-lying one-electron Kohn–Sham eigenstates up to the Fermi level. Each excited state $|\Psi^{(i)}\rangle$ is then constructed by creating electron–hole (e – h) pairs using the unoccupied Kohn–Sham eigenstates. Thus, the $E_0 - E_i$ term in the denominator is simply the energy difference between the occupied and unoccupied eigenvalues associated to the particular e – h excitation [13, 18–20]. The perturbative expansion may then be written in terms of the GS Kohn–Sham eigenstates $|kn\sigma\rangle$ as follows:

$$\Delta E_{\text{SO}}^{(2)} = \frac{1}{N_k} \sum_k \sum_{n,n'}^{N_b} \sum_{\sigma,\sigma'} \frac{f(\epsilon_{kn\sigma})[1 - f(\epsilon_{kn'\sigma'})]}{\epsilon_{kn\sigma} - \epsilon_{kn'\sigma'}} \times \langle kn\sigma | H_{\text{SO}} | kn'\sigma' \rangle \langle kn'\sigma' | H_{\text{SO}} | kn\sigma \rangle, \quad (5)$$

where σ, σ' stand for the spin indices.

The second-order formula given by equation (5) is applicable only to a non-degenerate GS. A degenerate GS in an extended metallic system happens when there is a band crossing at a certain k -point precisely at the Fermi level and this band pair is coupled by H_{SO} (i.e. the corresponding matrix element is not zero). This can happen eventually, and in this situation the eigenstate pair should be treated separately by first-order degenerate state perturbation theory. However, in a calculation with a large N_k the contribution to $\Delta E_{\text{SO}}^{(2)}$ of these exactly degenerate states would be negligible, since only a handful of band crossings are expected at the Fermi level, and they contribute with a factor of order ξ/N_k [37]. A sufficiently fine k -grid can map the spin–orbit band splitting effect nearby the crossing, so that equation (5) can be safely used.

In practice, it is convenient to express equation (5) in a basis whose elements have well defined lm quantum numbers (spherical harmonics Y_{lm}). A natural choice are AOs, which already constitute the basis set in a number of DFT-based packages, leading to Bloch Kohn–Sham eigenstates of the form:

$$|kn\sigma\rangle = \frac{1}{\sqrt{N_k}} \sum_{\mathbf{R}} e^{i\mathbf{k}\cdot\mathbf{R}} \sum_{\alpha}^{N_{\alpha}} c_{\alpha}^{n\sigma}(k) |\alpha(\mathbf{R}), \sigma\rangle, \quad (6)$$

where $\mathbf{R}$ runs over the lattice vectors, $|\alpha(\mathbf{R})\rangle$ denotes an AO located in unit cell $\mathbf{R}$ and N_{α} is the total number of AOs in the basis set. Inserting equation (6) into 5 yields:

$$\Delta E_{\text{SO}}^{(2)} = \frac{1}{N_k} \sum_k \sum_{\sigma\sigma'} \sum_{n,n'}^{N_b} \frac{f(\epsilon_{kn\sigma})[1 - f(\epsilon_{kn'\sigma'})]}{\epsilon_{kn\sigma} - \epsilon_{kn'\sigma'}} \sum_{\alpha,\beta,\alpha',\beta'}^{N_{\alpha}} \langle \alpha | H_{\text{SO}}^{\sigma\sigma'}(k) | \beta \rangle \langle \alpha' | H_{\text{SO}}^{\sigma'\sigma}(k) | \beta' \rangle n_{\alpha\beta}^{nn'\sigma\sigma'}(k) n_{\alpha'\beta'}^{n'n\sigma'\sigma}(k), \quad (7)$$

where the k -space $H_{\text{SO}}(k)$ matrix elements are given by:

$$\langle \alpha | H_{\text{SO}}^{\sigma\sigma'}(k) | \beta \rangle = \frac{1}{N_k} \sum_{\mathbf{R}} e^{i\mathbf{k}\cdot\mathbf{R}} \langle \alpha(0), \sigma | H_{\text{SO}} | \beta(\mathbf{R}), \sigma' \rangle \quad (8)$$

and the *generalized projected charges* by:

$$n_{\alpha\beta}^{nn'\sigma\sigma'}(k) = (c_{\alpha}^{n\sigma}(k))^* c_{\beta}^{n'\sigma'}(k). \quad (9)$$

It is usual to further assume the so-called on-site approximation, whereby the $\mathbf{l}_i \cdot \mathbf{s}_i$ operators only mix states within the same l -shell of a given atom contained in the origin unit cell. Equation (8) then becomes:

$$\langle \alpha | H_{\text{SO}}^{\sigma\sigma'}(k) | \beta \rangle \approx \langle \alpha(0), \sigma | H_{\text{SO}} | \beta(0), \sigma' \rangle \approx \xi_{\alpha,l} \langle \alpha l m \sigma | \mathbf{l} \cdot \mathbf{s} | \beta l' m' \sigma' \rangle \delta_{\alpha\beta} \delta_{ll'} \quad (10)$$

where indices α, β in the last term now refer to the principal quantum number in a given atom (in a multi- ζ scheme, also the particular ζ [38]), and lm stand for the orbital and magnetic quantum numbers of each AO. $\xi_{\alpha,l}$ is the SOI strength for this l -shell resulting from the integration of the radial part in the $\langle \alpha l m \sigma | H_{\text{SO}} | \alpha l m' \sigma' \rangle$ matrix elements (independent of mm' and $\sigma\sigma'$). The angular part of these matrix elements, $\langle \alpha l m \sigma | \mathbf{l} \cdot \mathbf{s} | \alpha l m' \sigma' \rangle$, take simple analytical expressions and tabulated formulas as a function of the spherical harmonics Y_{lm} involved can be found, for example, in [39, 40]. The on-site approximation simplifies considerably the 2PT formula:

$$\Delta E_{\text{SO}}^{(2)} = \frac{1}{N_k} \sum_k \sum_{\sigma\sigma'} \sum_{n,n'} \frac{f(\epsilon_{kn\sigma})[1 - f(\epsilon_{kn'\sigma'})]}{\epsilon_{kn\sigma} - \epsilon_{kn'\sigma'}} A^{nn'\sigma\sigma'}(k) A^{n'n\sigma'\sigma}(k), \quad (11)$$

where we have defined:

$$A^{nn'\sigma\sigma'}(k) = \sum_{\alpha l} \xi_{\alpha l} \sum_{mm'}^{2l+1} \langle \alpha l m \sigma | \mathbf{l} \cdot \mathbf{s} | \alpha l m' \sigma' \rangle n_{\alpha l m \alpha l m'}^{nn'\sigma\sigma'}(k). \quad (12)$$

We observe that the 2PT equations (7) and (11) are perturbative in the SOI strength, which appears explicitly in the form of the parameters $\xi_{\alpha l}$ in this equation.

Next, we consider the case when the unperturbed spin-polarized calculation is realized employing a plane-wave basis set, as many DFT codes do. Instead of using a Bloch-function representation of the Kohn–Sham eigenstates, we use a set of N_w maximally localized Wannier functions (MLWF) as formulated in [41]. MLWFs are constructed to yield the exact eigenvalues as the *ab initio* calculation. Usually, a previous disentanglement procedure is carried out, whereby a handful of relevant bands within an energy window are isolated from the rest [42]. For the systems under study, we focus on the bands that originate from the d -valence electrons of both metal atoms (allowing also for some degree of s – d hybridization) and belong to a window of about 10 eV below and 5 eV above the Fermi energy. Afterwards, it is straightforward to obtain new Bloch functions on a k -grid as dense as desired by interpolation [43]. This procedure allows us to estimate the 2PT MAE using as input solely a scalar-relativistic first-principles calculation and does not require a highly dense 1BZ k -sampling.

The j th MLWF localized at the unit cell $\mathbf{R}$ that results from band disentanglement and wannierization for states with spin σ is:

$$|w_j^\sigma(\mathbf{R})\rangle = \frac{1}{N_k} \sum_k e^{-i\mathbf{k}\cdot\mathbf{R}} \sum_n^{N_b} Q_j^{n\sigma}(k) |kn\sigma\rangle, \quad (13)$$

where $|kn\sigma\rangle$ stands for the Kohn–Sham eigenstates already interpolated in the dense k -grid [43] and $Q_j^{n\sigma}(k)$ are the coefficients that relate the Wannier and Bloch functions.

Typically, atomic-like wavefunctions, formed by a radial function and spherical harmonics Y_{lm} to describe the angular component, are used to initialize the wannierization procedure. Here, we use d -orbitals centred at the atomic sites and a few s -waves at interstitial positions. The purpose of the latter functions is to facilitate the wannierization and will not take part in the 2PT MAE calculation. We fix $l = 2$ and drop this index in the following. Thus, the j label accounts for the α -th atom in the cell $\mathbf{R}$ and the $m = 0, \pm 1, \pm 2$ quantum number. If the deviation of the MLWFs from actual atomic wavefunctions is small, we can approximate the matrix elements $\langle w_{\alpha m}^\sigma(\mathbf{R}) | H_{\text{SO}} | w_{\alpha m'}^{\sigma'}(\mathbf{R}) \rangle$ by the ones in the AO representation $\langle \alpha m \sigma | \mathbf{l} \cdot \mathbf{s} | \alpha m' \sigma' \rangle$ and take advantage of their simple analytic expressions [39, 40]. Note that, in general, the resulting MLWFs do not keep a well-defined orbital character because they have to account for both the intra- and inter-AO hybridization present in the system [44]. Nevertheless, a suitable choice of axes in the systems under study allows to obtain MLWFs that keep the AO character and justify this approximation. Substituting equation (13) in (5) and using this approach, the second-order energy correction associated to the SOI is

$$\Delta E_{\text{SO}}^{(2)} = \sum_{\alpha_1 \alpha_2} \sum_{\sigma \sigma'} \sum_{m_1 m_2} \sum_{m'_1 m'_2} \xi_{\alpha_1} \xi_{\alpha_2} F_{m_1 m_2 m'_1 m'_2}^{\sigma \sigma' \alpha_1 \alpha_2} \langle \alpha_1 m'_1 \sigma' | \mathbf{l} \cdot \mathbf{s} | \alpha_1 m_1 \sigma \rangle \langle \alpha_2 m'_2 \sigma' | \mathbf{l} \cdot \mathbf{s} | \alpha_2 m_2 \sigma \rangle, \quad (14)$$

where the m_i indexes run over the 5 d -orbitals of each atom α_i in the unit cell. The F coefficients contain the details of the basis change from Kohn–Sham states to MLWF states and, implicitly, they allow us to use a dense k -grid by interpolation:

$$F_{m_1 m_2 m'_1 m'_2}^{\sigma \sigma' \alpha_1 \alpha_2} = \frac{1}{N_k} \sum_k \sum_{nn'} \frac{f(\epsilon_{kn\sigma})[1 - f(\epsilon_{kn'\sigma'})]}{\epsilon_{kn\sigma} - \epsilon_{kn'\sigma'}} Q_{\alpha_1 m_1}^{n\sigma}(k) (Q_{\alpha_1 m'_1}^{n'\sigma'}(k))^* Q_{\alpha_2 m_2}^{n\sigma}(k) (Q_{\alpha_2 m'_2}^{n'\sigma'}(k))^*. \quad (15)$$

Equation (14) is similar to the 2PT MAE formula for extended systems developed by van der Laan [20], and here we generalize the result to the case of more than one atom per unit cell. It is also straightforward to show that the on-site approximation equation (11) reduces to the above expression after replacing the Bloch coefficients $c_{\alpha}^{n\sigma}(k)$ in equation (9) by the $Q_j^{n\sigma}(k)$ ones and restricting the summation over the angular momentum numbers to the $l = l' = 2$ case.

Table 1. Unit cell lattice parameters (see figure 1) of the considered model bulk systems and calculation parameters used in the wannierization. n_s is the number of s -wave-like Wannier functions, introduced in addition to the d -orbital-like ones, placed at interstitial sites of the structure. $[w_0, w_1]$ are the frozen windows used for disentanglement with respect to the Fermi energy. Two intervals are shown for FeAu that correspond to different windows for the spin-majority and spin-minority bands, respectively. k_1 is the grid used in the reference DFT calculation and k_2 the interpolated grid used to evaluate the MAE in the 2PT approximation. $p_{\min}$ is the minimum projection factor p_{amo} (equation (16)) found for each system.

	FeCo	FeCu	FePd	FePt	FeAu
a (Å)	2.680	2.553	2.751	2.722	2.885
c/a	1.2	1.339	1.327	1.364	1.328
n_s	3	4	3	2	3,4
$[w_0, w_1]$ (eV)	[−5.2, 2.8]	[−10.0, 3.5]	[−6.6, 2.4]	[−5.8, 2.2]	[−3.4, −1.1], [−1.4, 1.6]
k_1	$16 \times 16 \times 14$	$16 \times 16 \times 12$	$16 \times 16 \times 12$	$16 \times 16 \times 12$	$16 \times 16 \times 12$
k_2	$40 \times 40 \times 33$	$36 \times 36 \times 28$	$36 \times 36 \times 27$	$40 \times 40 \times 30$	$36 \times 36 \times 27$
$p_{\min}$	0.88	0.82	0.82	0.90	0.85

Table 2. Geometry of the considered thin film models and calculation parameters used in the wannierization. A supercell of height 22.5 Å is used. Here, d is the distance between atomic planes. The other parameters description is similar to that of table 1. Frozen windows are used only in the FePt models.

	FeCo(111)	FeCo(100)	FePt(111)	FePt(100)
a (Å)	2.50	2.68	2.78	2.722
d (Å)	2.094	1.674	2.128	1.856
n_s	3	2	4	3
$[w_0, w_1]$ (eV)	—	—	[−8.6, 0.9], [−8.6, 1.9]	[−5.8, 0.2], [−7.8, 2.7]
k_1	$16 \times 16 \times 1$	$16 \times 16 \times 1$	$16 \times 16 \times 1$	$16 \times 16 \times 1$
k_2	$96 \times 96 \times 1$	$96 \times 96 \times 1$	$96 \times 96 \times 1$	$96 \times 96 \times 1$
$p_{\min}$	0.92	0.91	0.88	0.87

Note that equation (14) (or equation (7)) is a ‘four-legged’ expression in the sense that is contributed by two different e – h pairs. There are other 2PT formulations based on the use of a localized basis set of orbitals [13, 15, 18, 19]. However, it is worth to mention that our formulation of the MAE does not neglect spin-flip contributions, unlike the one proposed by Bruno [18]. Formulas that neglect wavefunction phase effects in the Kohn–Sham-to-local-basis projection have also been proposed [13, 15]. By doing so, the ‘four-legged’ equation (14) becomes only ‘two-legged’ and equation (15) can be written in simpler terms, namely the projected densities of states on the local orbitals.

3. Computational details

In all the procedures described in this section, to prevent the MAE values from being biased by the structural parameters, we have kept the bulk $L1_0$ lattice constants a , c fixed in all calculations (see figure 1 and table 1). The model for FeCo has the Fe *bcc* unit cell volume and $c/a = 1.2$ to maximise the anisotropy, as suggested by the literature on strain effects [30]. For FeCu, we keep the Cu–Cu as in bulk *fcc* Cu and $c/a = 1.34$ [45]. Finally, we use published lattice constants for FePd, FeAu [46] and FePt [47]. The interplanar distance of the FeCo and FePt bilayer models with (100) structure has been set to $d = c/2$. For the (111) films, the Co and Pt bulk lattice constants have been used and the interplanar distance has been optimized (see table 2).

Two DFT codes have been used in this work: SIESTA–Green (SG) [38, 48] and VASP [49, 50]. The former uses multi- ζ non-orthogonal strictly localized numerical AOs as basis set and replaces core electrons by pseudo-potentials, while the latter uses plane-waves and projector-augmented wave potentials to describe the ion cores [51]. Both codes feature SOI implementations [48, 52] that allow to obtain the MAE values directly from equation (2) or the SOI-corrected eigenvalues of equation (3). By working with both codes we ensure that the conclusions about the MCA are not biased by the basis set type. The exchange and correlation functional used in all calculations is that of Perdew, Burke and Ernzerhof [53].

In the VASP calculations the p semi-core states are included as valence electrons. We have set the plane-wave energy cut-off to 400 eV in all the systems, except for 420 eV in FeAu, and suitable k -point Monkhorst–Packgrids [54] according to each lattice dimensions and calculation type ($24 \times 24 \times 20$) for FeCo and ($24 \times 24 \times 18$) for the other $L1_0$ units cells, and ($48 \times 48 \times 1$) for the thin film calculations). The tetrahedron method with Blöchl corrections is used to obtain the Fermi level [55]. For the SG calculations we have adopted a double- ζ polarized scheme to generate the AO basis set using a confinement energy of 100 meV although, as

Table 3. SG values of the atomic SOI strength parameter ξ_{Me} (Me=Co, Cu, Pd, Pt, Au) and VASP values of the atomic spin and orbital magnetic moments, μ_S and μ_L , respectively, in Bohr magnetons (μ_S values are obtained from calculations without SOI). The last column shows an approximated MAE obtained from the expression $-\sum_{\alpha} \frac{\xi_{\alpha}}{4} [\mu_L^x(\alpha) - \mu_L^z(\alpha)]$, where the index α runs over the Fe and Me atoms, with $\xi_{\text{Fe}} = 59.65$ meV.

	ξ_{Me} (meV)	μ_S (Fe)	μ_S (Me)	μ_L^x (Fe)	μ_L^x (Me)	μ_L^z (Fe)	μ_L^z (Me)	MAE (meV)
FeCo	74.12	2.74	1.67	0.053	0.077	0.064	0.088	0.37
FeCu	110.44	2.55	0.16	0.045	0.009	0.055	0.011	0.20
FePd	191.36	3.00	0.38	0.061	0.030	0.069	0.027	−0.02
FePt	537.18	2.93	0.40	0.057	0.056	0.060	0.044	−1.57
FeAu	615.05	2.98	0.03	0.045	0.037	0.065	0.029	−0.93

opposed to VASP, no p semi-core states are considered. Pseudo-core corrections are included for all the atoms involved, while a very fine real space mesh is employed by setting the mesh cut-off to 4000 Ry.


In the SG case, SOI matrices are calculated under the fully-relativistic pseudo-potential (FR-PP) method described elsewhere [48]. This approach goes beyond the on-site approximation [56] (equation (10)) as it takes into account intra- and inter-atomic interactions between different l -shells. Although the off-site terms tend to be small, test calculations show that neglecting them can induce errors in the MAE of around 0.2 meV or even larger (around 1 meV) in particular cases. Nevertheless, the on-site approximation allows to extract the SOI strengths $\xi_{\alpha b}$ which we provide in table 3 for the d orbitals.

Even when working with the FSC method for SOI, the calculation parameters must be carefully tested. The Fermi energy smearing is a decisive technical factor for the MAE of some of the systems. This issue has been addressed with both codes for the FSC and FT methods. We find satisfactory convergence when the tetrahedron method is used for the FSC MAE with VASP [55]. By doing so, we avoid kT -dependence in the resulting MAE values (we have checked that the total energy extrapolation to $kT = 0$ gives, in general, good agreement with the results of the tetrahedron method). With SG, since the use of finer k -point grids can be afforded at a reasonable computational and memory cost, a high convergence could be systematically achieved in the k -grid. Convergency values below 0.01 meV are obtained with kT values entering the Fermi–Dirac distribution function as low as 1 meV. In the FT calculations we find that the smearing function, whether Fermi–Dirac or Methfessel–Paxton of a given order [57], has a non-negligible influence, but it becomes less important for sufficiently fine k -grids and small kT . A detailed convergence analysis for all phases can be found in the Supplementary Information sections 1, 2 and figures 1–4 (stacks.iop.org/NJP/21/073054/mmedia).

For the more elaborate 2PT methodology, we have implemented equation (7) for the SG calculations and the semi-analytical form of equation (14) for VASP in combination with Wannier90 [41, 58]. The k -grids needed to obtain a faithful representation of the electronic structure with MLWFs can be less dense than the ones typically needed to obtain the MAEs. The latter, also used in the explicit evaluation of equations (14) and (15), can be chosen as dense as desired by MLWF interpolation [43]. Besides, due to the strongly hybridized d -bands in the L1₀ Fe-alloys, prior to wannierization it is useful to perform a disentanglement of the bands [42] within an energy window that contains the relevant states. A numerical drawback in the whole procedure is that the quality of the wannierization is system-dependent. Therefore, for each alloy we have chosen suitable settings, shown in table 1, to meet the usual sanity requirements of a wannierization, namely, little overlap between MLWFs (at least between the functions that emulate the d -orbitals), bandstructure reproducibility, and spatial localization. The same strategy has been adopted for the four thin films (see table 2).

It is worth mentioning that the five atomic d -orbital wavefunction geometries, i.e. the representations of the angular functions $Y_{2m}(\hat{r})$ in cartesian coordinates, depend on the convention taken for the OX, OY, OZ axes in each code. Obviously, the electronic structure that results from hybridization of the atomic wavefunctions must be independent of those conventions. However, if we align the crystallographic directions and the cartesian axes of VASP and Wannier90 as shown in figure 1, we can represent the bonding states as overlapping $Y_{2m}(\mathbf{r} - \mathbf{R}_{\alpha})$ functions localized at atomic positions $\mathbf{R}_{\alpha}$. Otherwise, the overlaps would happen for linear combinations of $Y_{2m}(\hat{r})$ functions at each site. In such case, the MLWFs that reproduce the electronic structure do not resemble the initial spherical harmonics and equation (14) cannot be applied directly: an intermediate step would be needed to account for the linear combinations of $Y_{2m}(\hat{r})$ functions. The axes choice of figure 1 makes this step unnecessary. Indeed, we can trace the MLWFs back to individual Fe and Me d -orbitals by visual inspection (see supplementary information figure 5), deviations being the result of the inter-atomic hybridization only, i.e. an effect of a purely physical origin, and not an spurious one caused by the axes convention. To quantify those deviations, we define the projections

$$p_{\alpha m \sigma} = |\langle w_{\alpha m}^{\sigma}(\mathbf{R}) | \alpha m \sigma \rangle|^2 \quad (16)$$

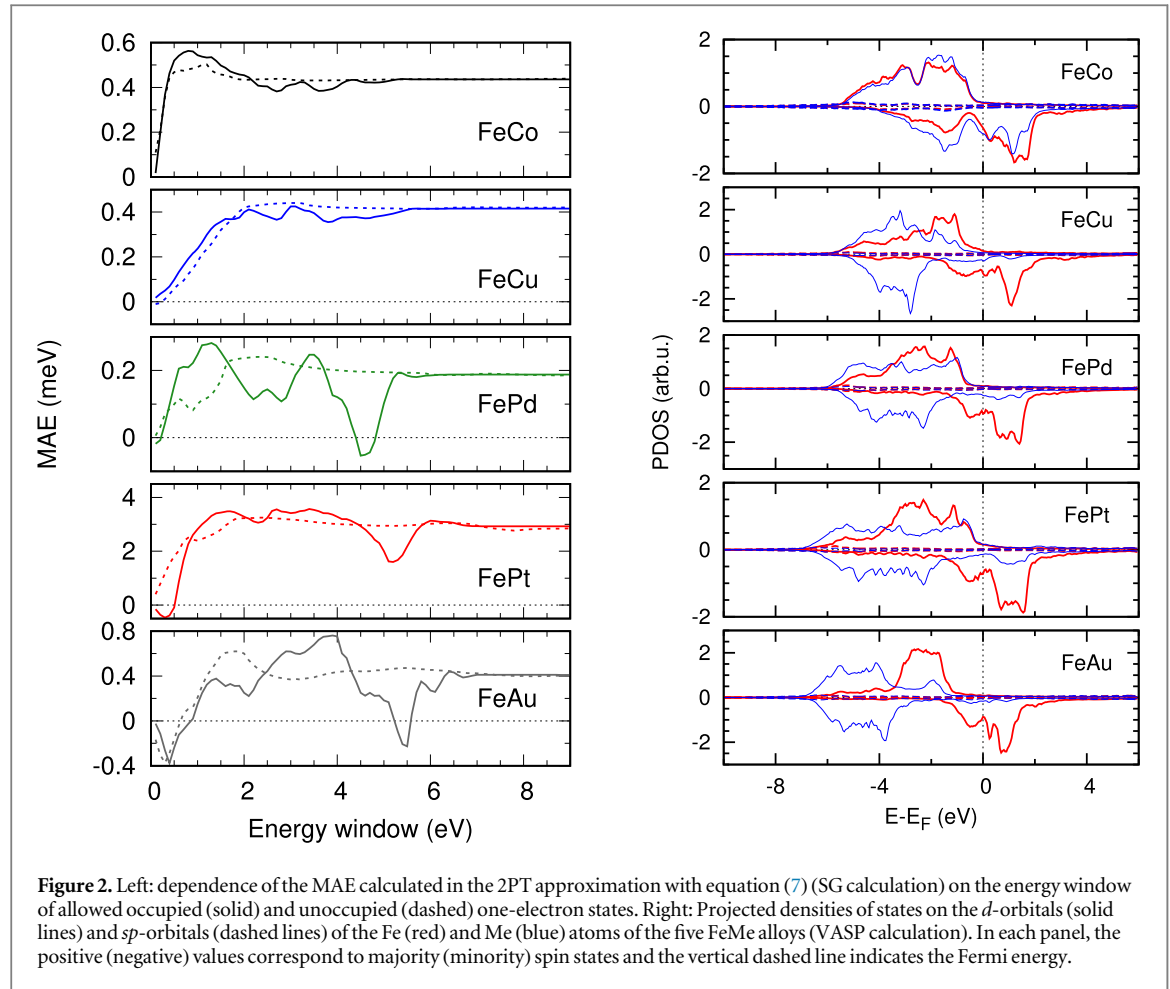

which range between zero and one. As shown in tables 1 and 2, despite the dispersive character of the bandstructures, in this work we find projections above 0.80 after wannierization.

4. Results and discussion


4.1. Neutral systems

Table 4 contains the collection of the MAE values of the $L1_0$ alloys calculated with the methodologies presented in section 3. All the approaches provide the same behaviour in the MCA of each alloy, albeit there are some quantitative differences in the corresponding MAE values, which will be discussed below. The easy magnetization axis is OZ in the five studied systems. Overall, MAE values are smaller than 0.5 meV except for FePt, a well-known prototype of large MCA, which shows a MAE of nearly 3 meV in good agreement with other *ab initio* values available in the literature [46–48, 59].

The first important observation is that the MAE of Fe-based $L1_0$ alloys is not directly correlated with the SO strength of the alloying metal. Indeed, it is the electronic structure what governs the MCA of these alloys, overruling the effect of the SO strength. We find larger MAE values for FeCo and FeCu than for FePd and FeAu in spite of $\xi_{\text{Pd,Au}}$ being larger than $\xi_{\text{Co,Cu}}$ (see table 3). In the case of FeCo it is known that a large MAE can be achieved by a strain on the cell along OZ. For $c/a = 1.2$, the geometry chosen for this work, a maximum is obtained because degenerate states coupled by H_{SO} lie on the Fermi level [30]. As a matter of fact, in this respect, FeCo is not an isolated case [15, 60].

The FSC values obtained in the VASP and SG calculations are in good agreement for FeCo, FeCu, and FePd, where discrepancies of 0.07 meV or smaller are found. For FePt and FeAu larger deviations of around 0.3 meV exist. The reason for this discrepancy is difficult to identify. Small quantitative differences in the band structures provided by both codes would be unimportant for most physical properties but, unfortunately, they become significant for the estimation of the MAEs.

However, the MAE values predicted by the FT method (see table 4) are, in general, very close to the FSC values, with typical deviations well below 0.1 meV. It is striking to find such a good agreement even for the heaviest metal systems, where the charge density change is expected to be larger. There are only a few exceptions,

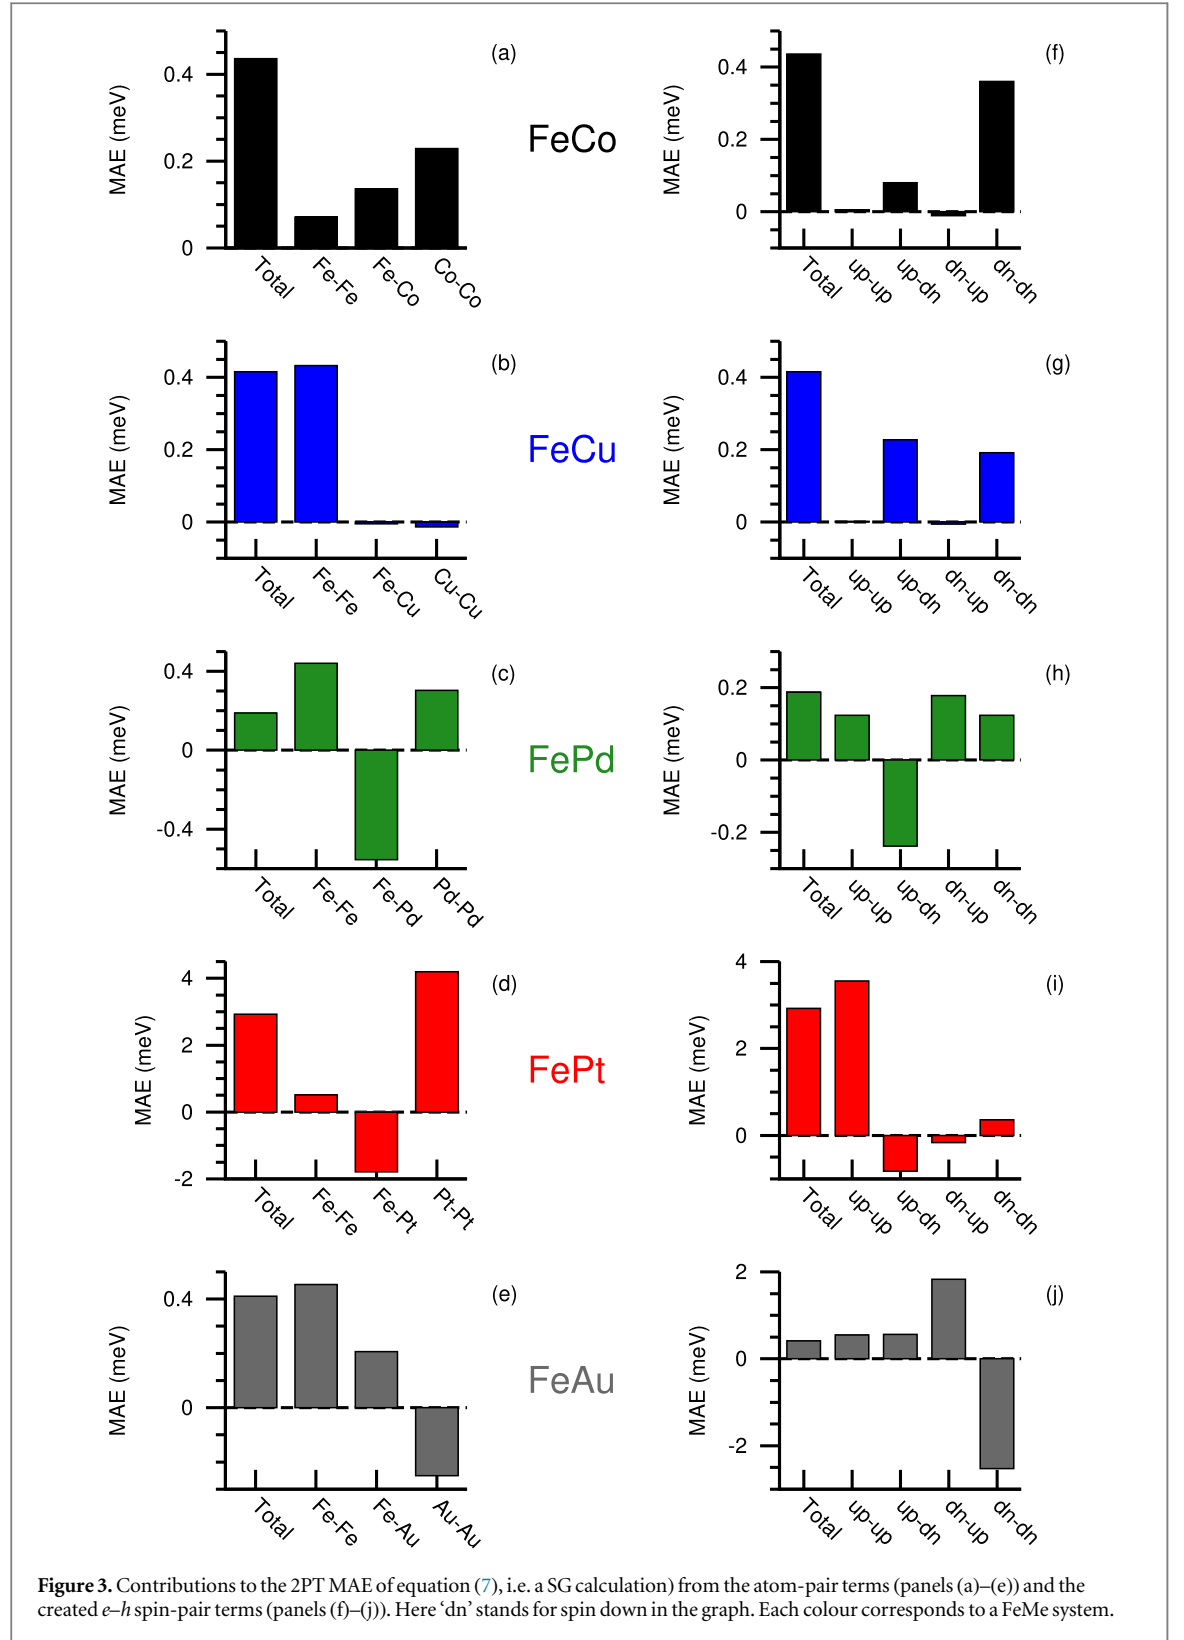

namely the VASP calculation for FePt, FeCo and FeAu and the SG one for FeAu for which, nonetheless, differences remain smaller than 0.2 meV. For the formers, we assign the discrepancy to calculation details rather than to the limitation of using the non-self-consistent charge density. Among the technical details, the smearing method used for the Fermi level determination is crucial, since the FT approach is sensitive to the small Fermi energy shift when magnetization occurs in one or other direction. In the FeAu case with SG, where full k -convergence is achieved, we may consider a 0.12 meV deviation as the upper limit to the accuracy of the FT, probably due to the larger ξ_{Au} SOI strength. Notwithstanding, the H_{SO} term is fully accounted for by this approach, although not self-consistently.

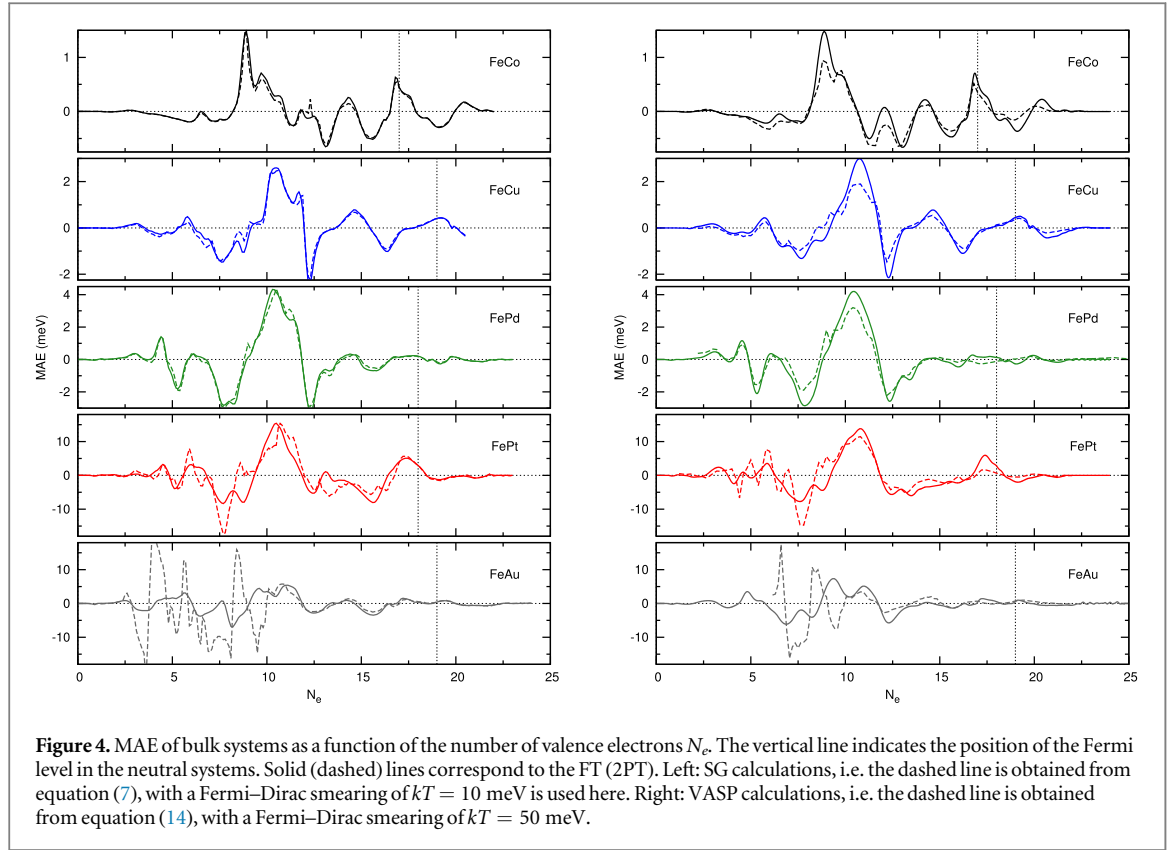


Figure 4. MAE of bulk systems as a function of the number of valence electrons N_v . The vertical line indicates the position of the Fermi level in the neutral systems. Solid (dashed) lines correspond to the FT (2PT). Left: SG calculations, i.e. the dashed line is obtained from equation (7), with a Fermi–Dirac smearing of $kT = 10$ meV is used here. Right: VASP calculations, i.e. the dashed line is obtained from equation (14), with a Fermi–Dirac smearing of $kT = 50$ meV.

Table 4. MAE values in meV for the bulk neutral systems. Labels SG and V indicate SIESTA–Green and VASP calculations, respectively, with the cut-off energy and k -point samplings discussed in the text. In the 2PT SG (VASP) calculations a Fermi–Dirac smearing with $kT = 10$ meV ($kT = 50$ meV) has been used.

	FSC (SG)	FSC (V)	FT (SG)	FT (V)	2PT (SG)	2PT (V)
FeCo	0.42	0.39	0.45	0.55	0.44	0.35
FeCu	0.38	0.45	0.42	0.45	0.42	0.38
FePd	0.22	0.16	0.20	0.13	0.19	−0.11
FePt	2.93	2.59	2.93	2.78	2.92	0.63
FeAu	0.20	0.50	0.36	0.62	0.41	0.76

Table 5 shows the MAE values for the thin films. The deviation of the FT values from the FSC ones is about 0.1 meV for FeCo and 0.3 meV for FePt bilayers. From these results, it is clear that the dimensionality reduction can undermine the performance of FT. This has been observed in Fe and Co adatoms on Rh(111), Pd(111) [12] and Pt(111) [61], too, with agreement between FT and FSC values largely depending on the adsorption site and atomic species [12]. We recall that under the FT the electron density is not allowed to relax when SOI is included. In the FSC calculation we expect these relaxations to be significant in the low-dimensional cases while in bulk 3D systems, with the concomitant symmetry constraints, they are strongly reduced. Therefore, we find the FT approach more reliable for the bulk (table 4) than for thin films (table 5).

Next, we address the performance of the 2PT approximation to the MAE, first focussing on the SG MAEs in table 4: MAE values are in almost perfect agreement with FSC and FT results, the only exception is the FeAu alloy with a 0.2 meV difference. Thus, the same behaviour between the FT and 2PT methods indicates that their accuracy is very similar despite the neglect of high-order H_{SO} terms in the latter, both providing excellent results at a much lower computational cost compared to the reference FSC calculations. The 2PT MAE values obtained with the wannierized bands from the VASP calculation yield worse agreement than the other methods becoming more pronounced the heavier the metal in the Fe alloy (see table 4). Specifically, the easy axis for FePd is switched to OX while the MAE of FePt is considerably underestimated and that of FeAu overestimated. Although this method allows the use of very dense k -point grids by interpolation, the quality of the wannierization procedure is crucial for numerical accuracy. Nonetheless, the main factor that undermines the final MAE values is the approximation in the H_{SO} matrix elements: the assumption that the MLWFs correspond to AOs with well-defined lm quantum numbers and, to a lesser extent, the on-site approximation

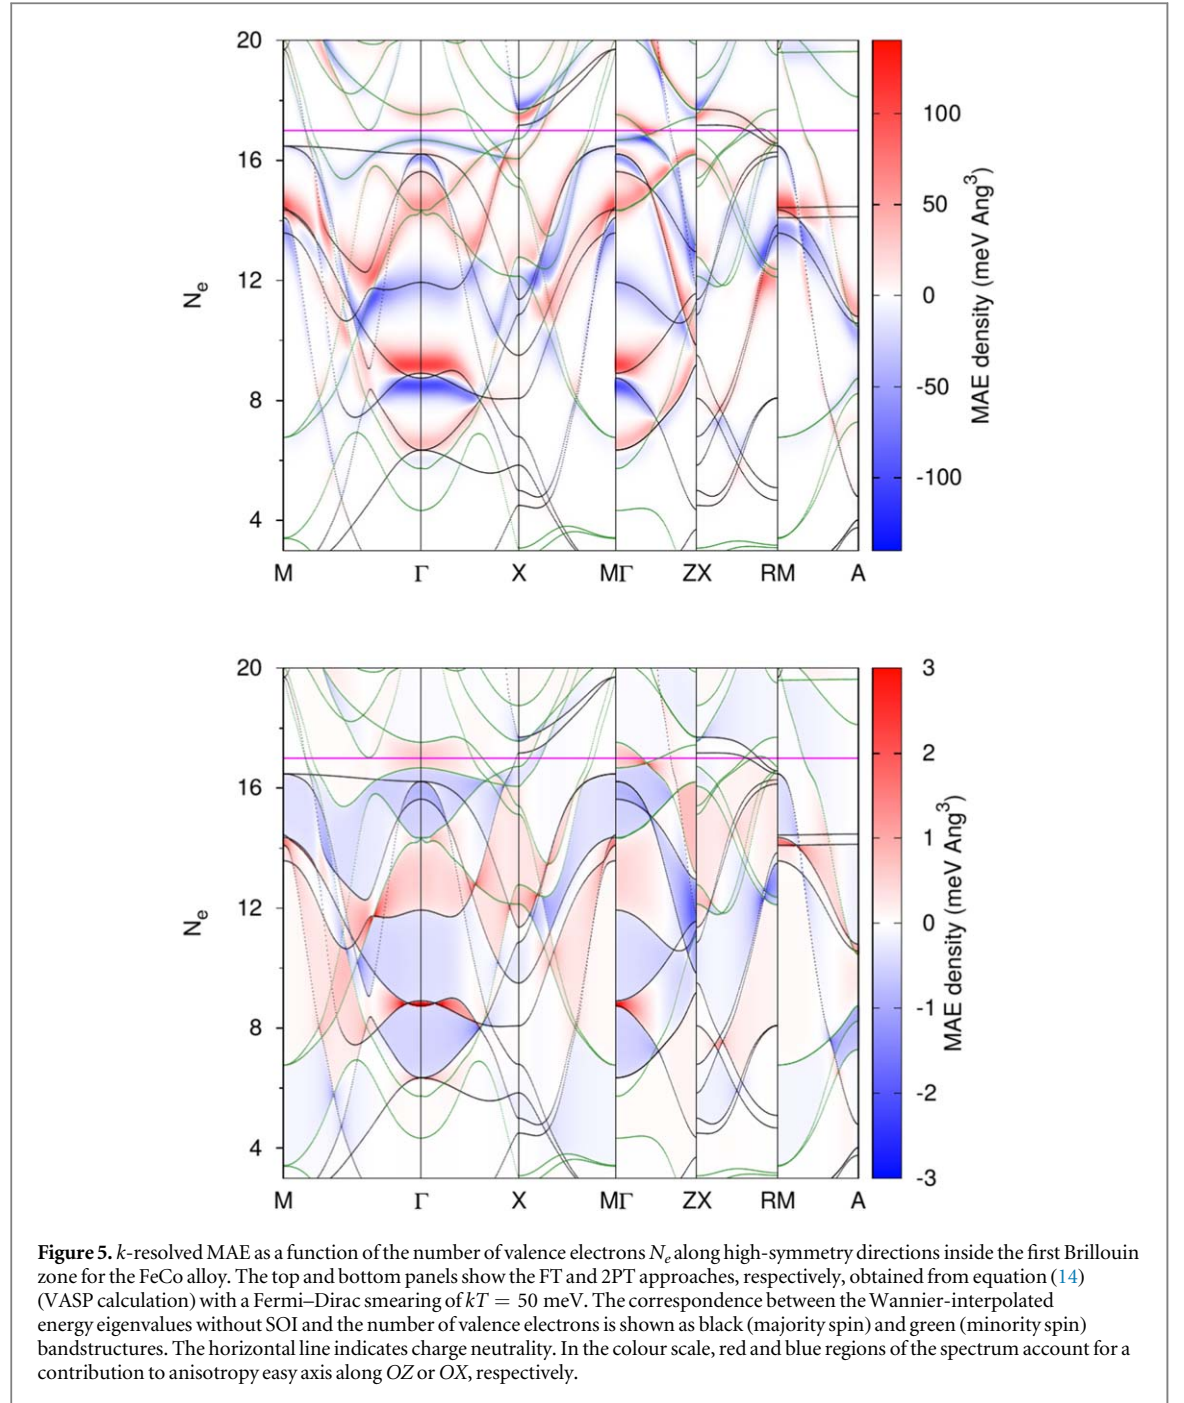


Table 5. MAE values in meV for the neutral bilayer models. Labels SG and V indicate SIESTA–Green and VASP calculations, respectively, with the parameters discussed in the text. As in the bulk structures, the 2PT SG (VASP) calculations used a Fermi–Dirac smearing with $kT = 10$ meV ($kT = 50$ meV).

	FSC (SG)	FSC (V)	FT (SG)	FT (V)	2PT (SG)	2PT (V)
FeCo(111)	−0.30	−0.41	−0.22	−0.36	−0.04	−0.12
FeCo(100)	0.42	0.38	0.51	0.39	0.76	0.38
FePt(111)	1.15	1.23	1.42	1.34	2.82	1.00
FePt(100)	2.95	2.35	3.39	2.24	6.00	1.75

(equation (10)) and the neglect of sp -orbital contributions. All in all equation (14) is a coarse approximation. Despite the apparent resemblance of MLWFs with atomic wavefunctions by visual inspection (see figure 5 in the supplementary information), the deformations of these ‘ d -orbitals’ are significant, due to the fact that Fe-alloys have strongly-hybridized bands. For FeCo and FeCu, nevertheless, the MAE behaviour in the energy

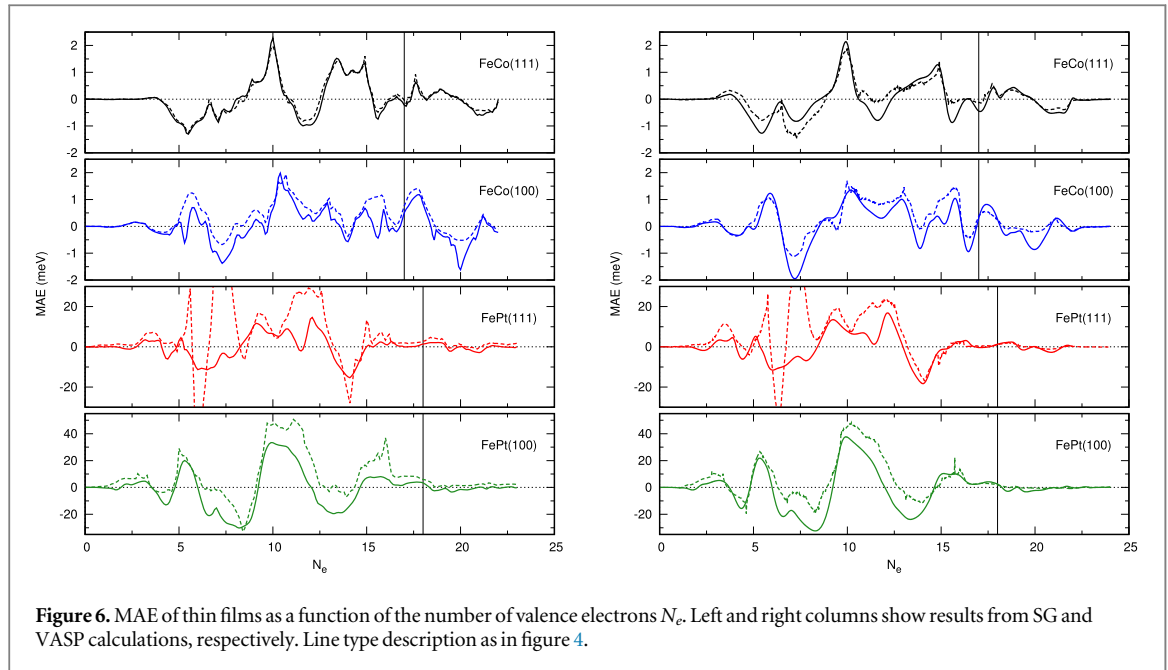


Figure 6. MAE of thin films as a function of the number of valence electrons N_v . Left and right columns show results from SG and VASP calculations, respectively. Line type description as in figure 4.

windows analysed is similar to the SG ones (not shown). The performance of the 2PT method for the thin films (table 5) is not as good as in the bulk case. As mentioned above, in a low-dimensional scenario we expect the spin–orbit effects on the electronic structure to be stronger. Thus, due to its perturbative nature, it is more difficult for the 2PT method to capture these effects fully.

Now, using the information provided by the $L1_0$ alloys we address the important issue of how close to the Fermi level are the states determining the MAE values, the above mentioned usual assumption. The 2PT-derived MAE is determined by eigenstates around the Fermi level within an energy range given by the SOI strength ξ and the $(\epsilon_{kn\sigma} - \epsilon_{kn'\sigma'})^{-1}$ factors. Indeed, equation (7) gives less weight to the e – h pairs coupled by H_{SO} matrix elements that lie farther in energy (the contributions of the energy prefactors are shown in figure 6 of the Supplementary Information). Intuitively, deep states in the valence band might be regarded as negligible for the MAE. However, a third factor needs to be considered: the available number of states. To analyse the competition of these three effects, we have calculated the 2PT MAE allowing only initial (final) states within an energy window below (above) the Fermi energy when evaluating equation (7). The results are shown in figure 2 (left) for the SG case, while those with VASP are qualitatively the same (not shown). When imposing an energy window on the occupied states, a plateau in the MAE value is not reached until the window is 5–7 eV wide, depending on the system. These energy ranges comprise the d -band widths below the Fermi level (see the densities of states (DOS) projected on the d -orbitals in figure 2 (right)). With heavier atoms, deeper states contribute non-trivially to the MAE, even reversing its sign, as it is the case of FeAu. Therefore, the final value of the MAE of each system depends on its electronic structure details, since the dispersion and binding energies of the individual band pairs coupled by H_{SO} largely vary from one system to another. The effect of constraining the accessible empty states in figure 2 is less dramatic and reveals a common behaviour in all the systems. With a window above the Fermi level, the MAE plateau is reached at ~ 2.5 eV. As shown in the DOS plots, this energy range corresponds to the empty spin-minority states of Fe in all the alloys and other empty metal d -states also contribute, although to a lesser extent, if available (Co and Pt).

Therefore, we conclude that, as a general rule, the high DOS counterbalances the decay of the $(\epsilon_{kn\sigma} - \epsilon_{kn'\sigma'})^{-1}$ factors and dominates over the ξ prefactors. We can see these trends in the systems under study. In brief, figure 2 shows that states distant from the Fermi level by as much as several eV (that is, spanning the whole d -band of the alloy) cannot be neglected in a 2PT calculation, not even in the case of atoms with weak SOI. We note also that, because of the DOS effect, the observed MAE for FeAu is not the largest, despite of the heavy Au atoms. From this figure, we conclude that the accessibility of empty Fe spin-minority states is a common feature that allows for sizeable MCAs in the Fe-based alloys, while the details of the occupied d -bands of each case determine the final MAE value.

Another appealing aspect of the 2PT formulation is that it allows to split the MAE into contributions arising from pairs of atoms in the metallic alloy: Fe–Fe, Fe–Me and Me–Me. This is straightforward when using MLWFs and equation (14) (see figures 7(a)–(e) in the supplementary information), while if equation (7) is used, the decomposition can be realized by restricting (α, α') to a given pair of atoms and performing the summation over all the other (β, β') AO contributions. The result is shown in figures 3(a)–(e). As expected, Fe and Co have a balanced weight on the final FeCo MAE, while Cu hardly contributes to that of FeCu. In the rest of alloys the

decompositions show the contribution we could expect from the knowledge of the electronic structure, at least qualitatively. The Pt–Pt and Fe–Pt terms are the main contributors in the FePt alloy, because ξ_{Pt} is an order of magnitude larger than ξ_{Fe} and because the d electrons of both species are strongly hybridized. We find, in agreement to [14], that the large contribution of the SOI of Pt atoms to the perpendicular anisotropy (OZ easy axis) is partially balanced by the effect of the Fe–Pt hybrid bands, which favour in-plane anisotropy. In FeAu, the Au–Au term is also very large due to the magnitude of ξ_{Au} , but now we see that the contribution of Fe–Au terms is weaker, since there is little hybridization with Au- d electrons.

Finally, we compare our perturbative results with the widely used 2PT equation by Bruno for bands of d -orbital character [18], which assumes that all the accessible holes are minority spin states. Therefore, it neglects e - h excitations that involve spin-flip, which leads to $\Delta E^{(2)} \propto \xi \langle L \rangle$. Table 3 shows the MAE values obtained in this approximation with the DFT-calculated AO moment values μ_L for each magnetization direction. Although the density of majority-spin states above the Fermi level is marginal (shown in figure 2), the results of the Bruno formula differ significantly from the other methods, and in some cases it does not even predict the correct easy magnetization axis. In addition to the breakdown of the approximation itself, we can ascribe the discrepancies to the tendency of DFT to underestimate orbital moment values.

Figures 3(f)–(j) shows the contributions of the e - h spin pairs to the MAE of equation (7) (the equivalent result with the MWLF approach is shown in the supplementary information figures 7(f)–(j)). We observe that the spin-flip terms have, indeed, a non-negligible contribution in all cases. In FeCo and FeCu the spin-down final (empty) states clearly dominate the total MAE value, since the contribution from the spin-up final states is almost negligible due to their very low DOS (see figure 2). However, the interpretation of the e - h spin pair contributions for the rest of alloys is less trivial; in the case of FePt, in particular, the up-up term surprisingly accounts for most of the MAE. A detailed energy-resolved analysis of this counterintuitive result (not shown) reveals that, despite the spin-down final states still yield the largest contributions in absolute value for all alloys, they tend to cancel or even provide net negative values (FePd, FePt, and FeAu) when integrated around the Fermi level, whereas the transitions involving spin-up final states increase in magnitude as the Me atom becomes heavier and tend to take positive values.

4.2. Non-neutral systems

Figure 4 shows the MAE as a function of the number of electrons N_e calculated for the $L1_0$ cases within the FT and the 2PT approaches. Here, we have followed a rigid band approach, in which the Fermi level is recalculated for each N_e employing the eigenvalues and eigenstates of the unperturbed neutral calculation. Hence, the plots represent the MAE behaviour of each alloy under conditions of doping or application of a bias voltage, which are common working conditions in magnetic devices, albeit, due to the rigid band approach, only small deviations from the neutral situation are physically meaningful. Nevertheless, this approach provides a deep understanding of the physical origin of the MCA and yields valuable information about the accuracy of the MAE values, as we show below. As expected from the discussion in the previous section, there are only small differences between the FT curves calculated with SG and VASP.

Switching of the easy magnetization axis occurs several times as a function of band filling in all cases. Interestingly, a MAE reversal already takes place by removal or addition of one or two electrons per unit cell. Furthermore, the MAE undergoes drastic changes in magnitude, even attaining values which are one order of magnitude larger than the neutral ones, specially in the $N_e \approx 10$ region where the d -bands show the highest density of states.

With a methodological aim in mind, the study of the MAE in the non-neutral case allows us to study the validity of the 2PT perturbative approach with greater confidence than in the neutral case, since now we can compare a MAE curve with a rich structure instead of just a single value. The SG 2PT curves (dashed lines in the left-hand panel of figure 4) are in very good agreement with the FT curves for FeCo, FeCu, and FePd, while large discrepancies appear when heavier atoms are present. This is particularly evident in FeAu for $N_e = 5 - 10$, which corresponds to the spectrum region where the d -bands of Au lie. Considering the strong dependence of the MAE on the electron band structure details discussed in the previous section and the fact that the agreement with FT is not homogeneous as N_e changes, both facts suggest that 2PT loses its validity for elements with strong SOI. Thus, the coincidence in the neutral-case FePt and FeAu MAEs could be considered to be fortuitous, in the sense that the coincidence is a consequence of the specific band structure of the alloy, as it is the case of FePt (also observed in [62]) and FeAu⁵.

⁵ In the FeAu alloy, the Au- d states are mostly confined in a band between -7 and -4 eV below the Fermi energy (see figure 2). On the one hand, those states are subject to strong couplings by SOI, since $\xi_{\text{Au}} = 615$ meV. On the other hand, because of the $(\epsilon_{kn\sigma} - \epsilon_{kn'\sigma'})^{-1}$ factors, those states have a weaker effect on the MAE for N_e values close to charge neutrality ($N_e = 19$) than for smaller N_e values. E.g. a band filling $N_e = 10$ corresponds to a downward shift of the Fermi level of -3.7 eV, close to the Au- d states. Therefore, fast sharp oscillations are observed in the MAE curve at $N_e = 5 - 10$, while smooth behaviour and apparent agreement with FT exists at $N_e > 12$. Importantly, this does not mean that the Au- d states have a negligible contribution, as evidenced by the absence of a plateau in the occupied states curve of the FeAu panel of figure 2, which represents the $N_e = 19$ case. For the FePt alloy, since the Pt- d band is less localized in energies, the disagreement between 2PT and FT is visible throughout the MAE(N_e) curve.

This restriction of the 2PT validity to light atoms is not a serious disadvantage. This approach facilitates the MAE evaluation with fine k -point grids and narrow smearing widths at a lower computational cost, since it requires a single DFT calculation *without* SOI. We recall that a weak MCA does not necessarily follow from a small ξ , as we see in the systems under study. In extended systems like the current ones, band dispersion governs the MCA.

Both FT and 2PT describe SOI with a perturbative treatment of either the charge density changes or the ξ parameter, respectively. At this point, it is important to note another fundamental difference between the FT and 2PT formalisms. In the former method, the eigenvalues change with the magnetization axis and some degeneracies may be broken. In the latter method, the unperturbed band structure is not explicitly modified. Instead, e - h pair excitations of the GS $|\Psi^{(0)}\rangle$ are induced by H_{SO} , with probabilities given by their matrix elements. In other words, 2PT is a many-body approach, while FT is a one-electron approach. Thus, if we take the limit of single ions and uniaxial anisotropy, the 2PT approach described here tends to the widely-used formalism of the spin hamiltonian for non-degenerate states $H_{ion} = DS_z^2 + E(S_x^2 - S_y^2)$ [63, 64]. This magnetic anisotropy model is widely used in the study of single-atom magnetism and spin excitations [21–23].

Visual evidence of the inherent difference between FT and 2PT is presented in figure 5. This figure shows, for the case of FeCo and the VASP-Wannier calculation, the MAE densities as a function of N_e in the reciprocal space along a few high-symmetry directions inside the 1BZ. To guide the eye, the bands without SOI have been transformed from energies to the corresponding filling N_e and superimposed on the MAE density graph. As expected, for the FT case (top panel) the regions of non-zero MAE are localized close to the unperturbed bands, and take positive or negative values depending on the relative H_{SO} induced shifts in the eigenvalues between the OZ and OX magnetization directions. The map also reveals abrupt switching of the MAE densities close to several band-crossings. For example, this happens near the Γ point and $N_e \simeq 9$, where a pair of majority spin bands is split by a few meV for magnetization along OZ. Since the splitting is nearly symmetric in energy about the non-perturbed bands, the contribution to MAE is negative as the bottom band is filled and changes sign when the upper one starts to become occupied. When both bands are completely filled the MAE vanishes. In the 2PT approach the MAE density (lower panel) takes a very different aspect since the bandstructure is not modified and, as shown by figure 2, e - h pairs with an energy difference as large as a few eV can contribute to MAE at a given N_e (see also supplementary information figure 6). Thus, the map presents broad plateaus with a non-negligible MAE density in areas devoid of bands, while sign changes are always localized precisely at the bands, since they take place when the combined e - h distribution functions (term $f(\epsilon_{k\sigma})[1 - f(\epsilon_{kn'\sigma'})]$ in equation (5)) also changes sign as the band is crossed. Nevertheless, for FeCo the two approaches yield a similar overall description of the $MAE(N_e)$ behaviour, as seen in the k -integrated curve of figure 4 (right), in spite of treating bandstructures in a different way by construction.

With the 2PT calculation that uses MLWFs poorer agreement is found in the profile of the $MAE(N_e)$ curves, due to the limitations of this methodology. Still, the qualitative behaviour is reproduced in all alloys except FeAu, where similar deviations as for the SG case are found (see right-hand panel of figure 4). Therefore, it could be used under suitable conditions to make predictions on the MAE behaviour as a function of doping or bias voltage at a low computational cost from a DFT calculation which does not include SOI. Those conditions are (i) weak SOI strength and (ii) resemblance between the MLWFs and Y_{2m} spherical harmonics. When the first condition is met, the MAE obtained in the on-site approximation (equation (10)) performs as accurately as FT. This has been checked with SG calculations (see Supplementary Information figure 8), where the drawback of point (ii) is not present. Interestingly, the effect of inter-atomic d -orbital hybridization on the MAE is well captured by this methodology via the F factors in equation (15), while the crude approximation done for the SOI matrix elements seems less important, as it can be deduced from the good agreement with the FT curves in the FeCo and FeCu panels of figure 4 (right).

Finally, we analyse the effect of low dimensionality in the non-neutral case. Figure 6 shows the MAE dependence on the number of electrons per unit cell for the four studied bilayers. As discussed above in section 4.1, the impact of SOI in the two-dimensional bandstructure is stronger, which is manifested in the large magnitude of the oscillations in the MAE curves of figure 6. Although FT is a less reliable method for the thin films, we observe the same main trend as in the bulk results of figure 4, namely, that the agreement is better for FeCo, since the SOI strength is inside the perturbative regime.

5. Conclusions

In this work, we have included the SOI in DFT calculations at different levels of approximation to obtain the magnetocrystalline anisotropy energies (MAE). As reference, we use fully-relativistic fully-self-consistent (FSC) calculations. We have examined the accuracy of a many-body second-order perturbation (2PT) treatment of the SOI on the scalar-relativistic GS and we have found that it is as good as the well established FT approach. In both

cases (2PT and FT), we have confirmed that an accurate Fermi level determination is crucial to obtain well converged MAE values.

As case studies, we have considered several FeMe tetragonal ferromagnetic alloys with $L1_0$ structure, as well as two FeMe (Me=Co, Pt) bilayers with (111) and (100) symmetry. By choosing Me=Co, Cu, Pd, Pt, and Au, we cover the scenarios of s - d and d - d hybrid band effects and a range of atomic SOI strength parameters ξ . We find that the 2PT approximation describes accurately the MAEs of FeCo, FeCu, ($\xi \sim 0.05$ eV) and satisfactorily that of FePd ($\xi \sim 0.1$ eV), but fails for the alloys containing $5d$ metals ($\xi \sim 0.5$ eV), while FT provides reliable MAE values in general and some minor quantitative discrepancies with respect to FSC values for the bilayers. The difference in the performance of the two approximations has the following origin: while 2PT is perturbative in ξ , FT is perturbative in the charge density changes by SOI.

The MAE in this family of alloys is determined not only by the empty spin-minority Fe states, which lie about 2 eV above the Fermi level, but also by the whole valence band, which lies several eV below the Fermi level. Thus, the MCA is determined by electronic states that lie from the Fermi level much further than the SOI strength parameter. The details of the bandstructure are, in essence, responsible for the final MAE value.

Finally, the 2PT approximation is sound enough to account for the anisotropy behaviour of the weak SOI alloys under deviations from charge neutrality. We show that magnetic switching can be induced by addition or removal of electrons. This effect could be tuned by, for example, doping or strain, to find an scenario under a minimal bias voltage. These properties have ample applications in magnetoelectric and magnetostrictive devices. The 2PT approximation to the SOI, when valid, can be used to study large numbers of these cases efficiently, as it uses as sole input a scalar-relativistic DFT calculation.

Acknowledgments

Discussions with G Teobaldi and M dos Santos Dias are acknowledged. MB-R and AA thank financial support from MINECO (grant number FIS2016-75862-P), the University of the Basque Country (UPV/EHU) and the Basque Government (IT-756-13). JIC thanks MINECO for grant MAT2015-66888-C3-1R. Computational resources were provided by the DIPIC computing centre.

References

- [1] Dzialoshinskii I E 1957 *Soviet Phys. JETP* **5** 1259–72
- [2] Moriya T 1960 *Phys. Rev. Lett.* **4** 228
- [3] Heide M, Bihlmayer G and Blügel S 2009 *Physica B* **404** 2678–83
- [4] Mokrousov Y, Zhang H, Freimuth F, Zimmermann B, Long N H, Weischenberg J, Souza I, Mavropoulos P and Blügel S 2013 *J. Phys. Condens. Matter* **25** 163201
- [5] Wang W G, Li M, Hageman S and Chien C L 2012 *Nat. Mater.* **11** 64–8
- [6] Pantel D, Goetze S, Hesse D and Alexe M 2012 *Nat. Mater.* **11** 28–93
- [7] Dieny B and Chshiev M 2017 *Rev. Mod. Phys.* **89** 025008
- [8] Mermin N D and Wagner H 1966 *Phys. Rev. Lett.* **17** 1133–6
- [9] Daalderop G H O, Kelly P J and Schuurmans M F H 1990 *Phys. Rev. B* **41** 11919–37
- [10] Li C, Freeman A J, Jansen H J F and Fu C L 1990 *Phys. Rev. B* **42** 5433–42
- [11] Weinert M, Watson R E and Davenport J W 1985 *Phys. Rev. B* **32** 2115–9
- [12] Błosiński P, Lehnert A, Dennler S, Rusponi S, Etzkorn M, Moulas G, Bencok P, Gambardella P, Brune H and Hafner J 2010 *Phys. Rev. B* **81** 104426
- [13] Takayama H, Bohnen K P and Fulde P 1976 *Phys. Rev. B* **14** 2287–95
- [14] Solov'yev I V, Dederichs P H and Mertig I 1995 *Phys. Rev. B* **52** 13419–28
- [15] Ke L and van Schilfgaarde M 2015 *Phys. Rev. B* **92** 014423
- [16] Inoue J i, Yoshioka T and Tsuchiura H 2015 *J. Appl. Phys.* **117** 17C720
- [17] Ke L 2019 *Phys. Rev. B* **99** 054418
- [18] Bruno P 1989 *Phys. Rev. B* **39** 865–8
- [19] Cinal M, Edwards D M and Mathon J 1994 *Phys. Rev. B* **50** 3754–60
- [20] van der Laan G 1998 *J. Phys.: Condens. Matter* **10** 3239–53
- [21] Jacobson P, Herden T, Muenks M, Laskin G, Brovko O, Stepanyuk V, Ternes M and Kern K 2015 *Nat. Commun.* **6** 8536
- [22] Ferrón A, Delgado F and Fernández-Rossier J 2015 *New J. Phys.* **17** 033020
- [23] Baumann S et al 2015 *Phys. Rev. Lett.* **115** 237202
- [24] Jia C, Sukhov A, Horley P P and Berakdar J 2012 *Europhys. Lett.* **99** 17004
- [25] Duan C G, Velez J P, Sabirianov R F, Mei W N, Jaswal S S and Tsymbal E Y 2008 *App. Phys. Lett.* **92** 122905
- [26] Faleev S V, Ferrante Y, Jeong J, Samant M G, Jones B and Parkin S S P 2017 *Phys. Rev. Mater.* **1** 024402
- [27] Herper H C 2018 *Phys. Rev. B* **98** 014411
- [28] Zhang Y N, Cao J X and Wu R Q 2010 *Appl. Phys. Lett.* **96** 062508
- [29] Wang H, Zhang Y N, Wu R Q, Sun L Z, Xu D S and Zhang Z D 2013 *Sci. Rep.* **3** 3521
- [30] Burkert T, Nordström L, Eriksson O and Heinonen O 2004 *Phys. Rev. Lett.* **93** 027203
- [31] Andersson G, Burkert T, Warnicke P, Björck M, Sanyal B, Chacon C, Zlotea C, Nordström L, Nordblad P and Eriksson O 2006 *Phys. Rev. Lett.* **96** 037205
- [32] Turek I, Kudrnovský J and Carva K 2012 *Phys. Rev. B* **86** 174430

- [33] Quintana A et al 2017 *Adv. Funct. Mater.* **27** 1701904
- [34] Duan C G, Velez J P, Sabirianov R F, Zhu Z, Chu J, Jaswal S S and Tsymbal E Y 2008 *Phys. Rev. Lett.* **101** 137201
- [35] Nakamura K, Shimabukuro R, Fujiwara Y, Akiyama T, Ito T and Freeman A J 2009 *Phys. Rev. Lett.* **102** 187201
- [36] Gamble S J, Burkhardt M H, Kashuba A, Allenspach R, Parkin S S P, Siegmann H C and Stöhr J 2009 *Phys. Rev. Lett.* **102** 217201
- [37] Wang D s, Wu R and Freeman A J 1993 *Phys. Rev. Lett.* **70** 869–72
- [38] Soler J M, Artacho E, Gale J D, García A, Junquera J, Ordejón P and Sánchez-Portal D 2002 *J. Phys.: Condens. Matter* **14** 2745
- [39] Abate E and Asdente M 1965 *Phys. Rev.* **140** A1303–8
- [40] Elsässer C, Fähnle M, Brandt E H and Böhm M C 1988 *J. Phys. F: Metal Phys.* **18** 2463
- [41] Marzari N and Vanderbilt D 1997 *Phys. Rev. B* **56** 12847–65
- [42] Souza I, Marzari N and Vanderbilt D 2001 *Phys. Rev. B* **65** 035109
- [43] Yates J R, Wang X, Vanderbilt D and Souza I 2007 *Phys. Rev. B* **75** 195121
- [44] Roychoudhury S and Sanvito S 2017 *Phys. Rev. B* **95** 085126
- [45] Errandonea D 1997 *Phys. Lett. A* **233** 139–42
- [46] Galanakis I, Alouani M and Dreyssé H 2000 *Phys. Rev. B* **62** 6475–84
- [47] Ayaz Khan S, Blaha P, Ebert H, Minár J and Šipr O C V 2016 *Phys. Rev. B* **94** 144436
- [48] Cuadrado R and Cerdá J I 2012 *J. Phys.: Condens. Matter* **24** 086005
- [49] Kresse G and Hafner J 1993 *Phys. Rev. B* **47** 558–61
- [50] Kresse G and Furthmüller J 1996 *Phys. Rev. B* **54** 11169–86
- [51] Blöchl P E 1994 *Phys. Rev. B* **50** 17953
- [52] Steiner S, Khmelevskyi S, Marsmann M and Kresse G 2016 *Phys. Rev. B* **93** 224425
- [53] Perdew J P, Burke K and Ernzerhof M 1996 *Phys. Rev. Lett.* **77** 3865–8
- [54] Monkhorst H J and Pack J D 1976 *Phys. Rev. B* **13** 5188
- [55] Blöchl P E, Jepsen O and Andersen O K 1994 *Phys. Rev. B* **49** 16223–33
- [56] Fernández-Seivane L, Oliveira M A, Sanvito S and Ferrer J 2006 *J. Phys: Condens. Matter* **18** 7999
- [57] Methfessel M and Paxton A T 1989 *Phys. Rev. B* **40** 3616–21
- [58] Mostofi A A, Yates J R, Pizzi G, Lee Y S, Souza I, Vanderbilt D and Marzari N 2014 *Comp. Phys. Commun.* **185** 2309–10
- [59] Burkert T, Eriksson O, Simak S I, Ruban A V, Sanyal B, Nordström L and Wills J M 2005 *Phys. Rev. B* **71** 134411
- [60] Gambardella P et al 2003 *Science* **300** 1130–3
- [61] Błoński P and Hafner J 2009 *J. Phys.: Condens. Matter* **21** 426001
- [62] Kota Y and Sakuma A 2014 *J. Phys. Soc. Japan* **83** 034715
- [63] Pryce M H L 1950 *Proc. Phys. Soc. A* **63** 25
- [64] Dai D, Xiang H and Whangbo M H 2008 *J. Comput. Chem.* **29** 2187–209