

PAPER • OPEN ACCESS

Radio-frequency characterization of a supercurrent transistor made of a carbon nanotube

To cite this article: M Mergenthaler *et al* 2021 *Mater. Quantum. Technol.* 1 035003

View the [article online](#) for updates and enhancements.

You may also like

- [Vortex-state-mediated Josephson effect](#)
Zhao Yang Zeng and Chong Zhang
- [Nonequilibrium supercurrent in a mesoscopic four-terminal triplet Josephson junction](#)
J. Wang, S. Liu and K. S. Chan
- [Zero-frequency supercurrent susceptibility signatures of trivial and topological zero-energy states in nanowire junctions](#)
Lucas Baldo, Luis G G V Dias Da Silva, Annica M Black-Schaffer et al.



Easy-to-use and Helium-3 free
cryogenics solutions

LEARN MORE

Materials for Quantum Technology



PAPER

OPEN ACCESS

RECEIVED

2 April 2021

REVISED

6 July 2021

ACCEPTED FOR PUBLICATION

9 August 2021

PUBLISHED

2 September 2021

Original content from this work may be used under the terms of the [Creative Commons Attribution 4.0 licence](#).

Any further distribution of this work must maintain attribution to the author(s) and the title of the work, journal citation and DOI.



Radio-frequency characterization of a supercurrent transistor made of a carbon nanotube

M Mergenthaler^{1,2,5,*} , F J Schupp¹ , A Nersisyan², N Ares¹ , A Baumgartner³ , C Schönenberger³ , G A D Briggs¹ , P J Leek² and E A Laird^{1,4,*}

¹ Department of Materials, University of Oxford, Oxford OX1 3PH, United Kingdom

² Clarendon Laboratory, Department of Physics, University of Oxford, Oxford OX1 3PU, United Kingdom

³ Department of Physics, University of Basel, Klingelbergstrasse 82, CH-4056 Basel, Switzerland

⁴ Department of Physics, Lancaster University, Lancaster LA1 4YB, United Kingdom

* Authors to whom any correspondence should be addressed.

⁵ Present address: IBM Quantum, IBM Research - Zurich, 8803 Rüschlikon, Switzerland.

E-mail: mme@zurich.ibm.com and e.a.laird@lancaster.ac.uk

Keywords: supercurrent transistors, carbon nanotubes, radio-frequency measurements, Josephson Junction

Supplementary material for this article is available [online](#)


Abstract

A supercurrent transistor is a superconductor–semiconductor hybrid device in which the Josephson supercurrent is switched on and off using a gate voltage. While such devices have been studied using DC transport, radio-frequency measurements allow for more sensitive and faster experiments. Here a supercurrent transistor made from a carbon nanotube is measured simultaneously via DC conductance and radio-frequency reflectometry. The radio-frequency measurement resolves all the main features of the conductance data across a wide range of bias and gate voltage, and many of these features are seen more clearly. These results are promising for measuring other kinds of hybrid superconducting devices, in particular for detecting the reactive component of the impedance, which a DC measurement can never detect.

1. Introduction

When a Josephson junction is fabricated from a semiconductor, its superconducting properties depend on the semiconductor's density of states. This principle is the basis of the supercurrent transistor [1], in which the junction's critical current is modulated by a nearby gate voltage, allowing the device to be switched between resistive and superconducting states. Supercurrent transistors are components of low-temperature electronics such as SQUID magnetometers [2] and gatemon qubits [3, 4]. They can be used to measure level crossings [5] and chiral states [6] in junctions containing quantum dots, and also to investigate correlated-electron behaviour such as charge localisation [7].


Josephson junctions based on nanotubes and nanowires have been previously characterised in direct-current (DC) transport [1, 2, 8]. Much greater sensitivity and speed can be achieved using the technique of radio-frequency (RF) reflectometry. Furthermore, DC transport is sensitive only to the conductance of a junction but reflectometry in series with the device is also sensitive to reactance, and therefore should enable measurements of quantum capacitance [9] and Josephson inductance [10]. This has been confirmed by measuring the changes in conductance and inductance associated with the onset of superconductivity in NbTiN/InSb nanowire Josephson junction [11]. The high-frequency impedance of nanowire Josephson junctions has also been investigated by integrating them into on-chip microwave cavities to measure the Andreev states [12–14]. More recently, a nanowire Josephson junction was measured in DC transport while simultaneously being embedded into a gatemon qubit [15], which allowed the mapping of critical current characteristics to qubit frequency behaviour as a function of applied gate voltage. Nevertheless, the low frequency RF behaviour of a supercurrent transistor, in which the Josephson junction is switched on and off using a gate voltage, has never been investigated.

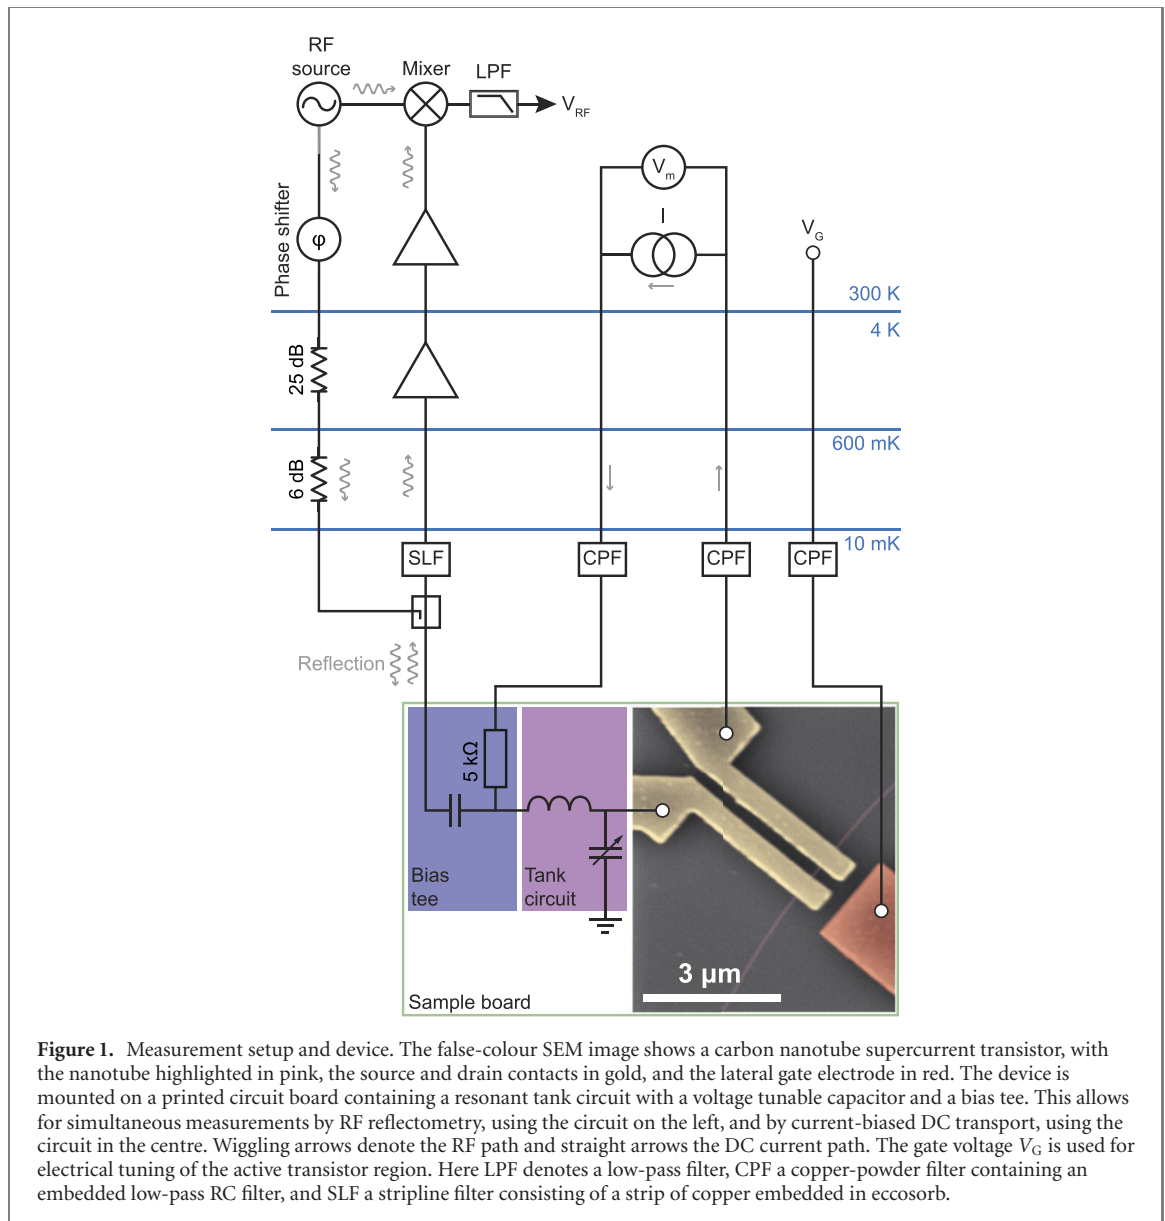

Here, we use simultaneous RF reflectometry and DC measurements to characterise a supercurrent transistor made of a carbon nanotube. We compare these two methods across the full operating regime of the device in bias and gate voltage. The RF data reproduces all the main features of the DC data, including the onset of superconductivity, a critical current that is tuned by a gate voltage and magnetic field, and the presence of Andreev reflections. In addition, the noise is much lower, as expected for a high-frequency measurement. These results show that a supercurrent transistor can be measured at RF without affecting its operation, and make RF techniques promising for rapidly characterising such devices under a range of conditions.

2. Device and measurement setup

Supercurrent transistors are fabricated using a single carbon nanotube contacted by superconducting electrodes as shown in figure 1. Device fabrication begins by growing nanotubes on a Si/SiO₂ substrate. The nanotubes are grown by chemical vapour deposition using Fe/Ru catalyst nano particles [16] at a temperature of 850 °C with methane as the precursor gas [17]. Bondpads and alignment markers are then patterned using electron beam lithography (EBL) and metalized with a bilayer of Ti/Au (10/50 nm). Following lift-off, SEM imaging is used to locate and select individual nanotubes for the transistors. Superconducting source and drain contacts and a lateral gate electrode are then patterned with EBL, developed, cleaned in an ultraviolet ozone chamber, and metallised with a superconducting Pd/Al (4/80 nm) bilayer. The edge-to-edge distance between the contacts is 300 nm. Before mounting the sample, the room-temperature resistances of the devices are measured to check the fabrication yield. Under atmospheric conditions and with the gate floating, roughly

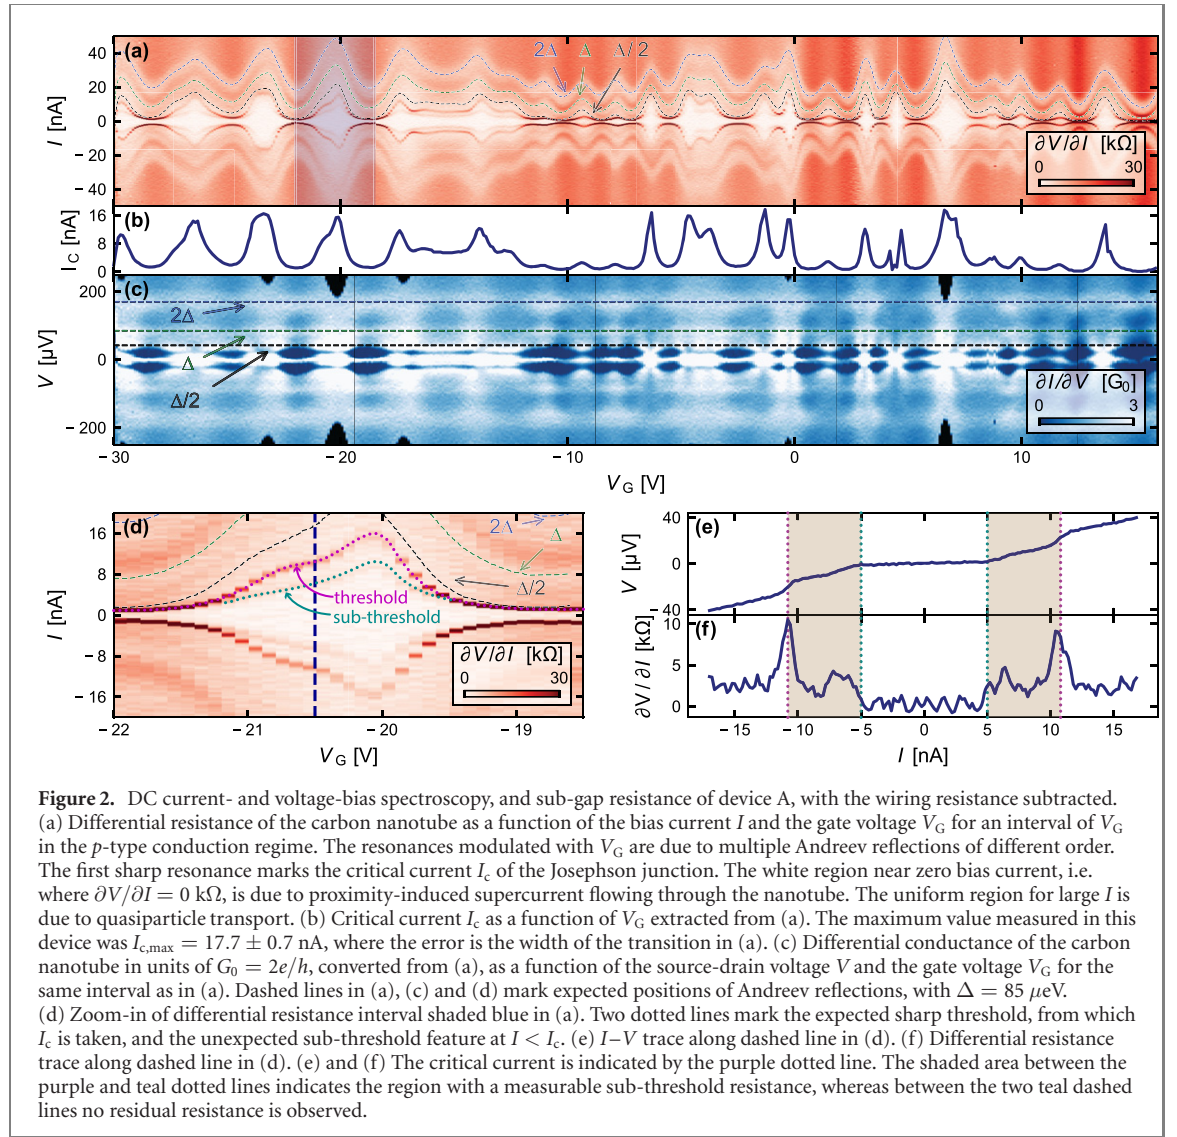

80% of the fabricated devices have a measurable conductance, with typical resistances between 7 kΩ and 100 kΩ. The two devices presented here (devices A and B) are identical in design and fabrication procedure, but originate from separate fabrication batches, demonstrating the reproducibility of the fabrication.

The transistors are measured in the sample puck of a Triton dilution refrigerator with a base temperature between 10 mK and 20 mK, using the circuit shown in figure 1, which allows simultaneous DC and RF measurements and *in situ* impedance matching for optimal sensitivity [18, 19]. All DC wires are filtered using printed-circuit-board copper powder filters [20] containing embedded RC filters. The devices are biased with a source-drain current I , and gated using a voltage V_G applied to the side gate. For DC resistance measurements, the voltage V_m at the top of the refrigerator is measured, and converted to a voltage V across the device by subtracting the voltage drop across the inline series resistance using

$$V = V_m - IR_S. \quad (1)$$

Here R_S is the series resistance, which incorporates all ohmic resistances in the current path, and is determined by a linear fit to the I - V trace in the supercurrent regime. It has the value $R_S = 10.72$ kΩ (15.71 kΩ) for device A (device B), which is consistent with the known inline resistance in the cryostat wiring. The differential resistance $\partial V/\partial I$ is calculated numerically.

To allow for RF reflectometry measurements, the device is mounted on a sample board containing an LC tank circuit and an in-built bias tee made from discrete chip components. The tank circuit exhibits a parallel impedance matching circuit, i.e. a voltage tunable capacitor, as in reference [18], which was used in order to tune the resonance into the optimal operation point. The loaded tank circuit exhibits a resonance frequency of 261.2 MHz with a quality factor of about 18. Reflectometry measurements are performed by injecting an RF tone via attenuated coaxial lines and a directional coupler, reflected from the tank circuit, and fed into a homodyne demodulation circuit to generate a demodulated voltage V_{RF} , cf figure 1. The RF power exciting the

tank circuit was approximately -117 dBm. Changes in resistance, capacitance, and inductance of the device modify the phase and amplitude of the reflected signal, and therefore the measured voltage V_{RF} [21–25].

3. DC spectroscopy

To determine typical properties of the nanotube supercurrent transistor, we first characterized one device (device A) using only DC measurements. In this measurement, the current bias is applied directly to the bond pad of the source contact, bypassing the bias tee and tank circuit. Figure 2(a) shows the differential resistance $\partial V/\partial I$ as a function of the bias current and gate voltage. This measurement was performed in a gate voltage region more negative than the location of the band gap, i.e. in the p -type conduction regime. As expected, we find the critical current is higher in this regime, because the Pd used as contacting layer in the superconducting leads yields a higher transparency of the contacts for holes [26], i.e. larger I_c . When I is close to zero, the differential resistance is small, indicating that the nanotube supports a supercurrent due to the proximity effect. The boundary of this region is marked by a sharp peak in the differential resistance, and is taken as the superconducting critical current I_c .


The critical current is strongly modified by changing V_G , as seen from figure 2(b). It ranges from less than 0.1 nA to a maximum of $I_{c,\text{max}} = 17.7$ nA. These strong but irregular variations indicate corresponding fluctuations in the nanotube density of states, such as arise from Coulomb blockade or from Fabry–Perot oscillations [1], cf supplementary material. The maximum critical current is higher than in most previous experiments with nanotube junctions [2, 27], although a larger critical current of 30 nA has been achieved using niobium contacts [28]. This is a strong indication of high-transparency contacts between the superconducting leads and the nanotube, and demonstrates the quality of the contact provided by the Al/Pd bi-layer combined with a UV ozone cleaning prior to contact metal deposition. This progress in materials and fabrication methods allows for the integration of such nanotube Josephson junctions into more complex hybrid superconducting devices such as superconducting qubits [29]. The large measured critical current may also indicate that this quantity depends on the number of walls of the nanotube. We did not measure the wall number or the nanotube diameter in our devices, and it is possible that the nanotube is multi-walled and that this allows for a larger critical current. The average critical current observed across the full region of V_G covered in figure 2(b) is $\langle I_c \rangle = 4.7$ nA. The fact that I_c depends on V_G confirms that the device is a supercurrent transistor.

For values of I greater than I_c , there is a series of broad dips in the differential resistance, consistent with multiple Andreev reflections [1, 8, 30]. To confirm this interpretation, figure 2(c) shows the same data plotted against the source-drain voltage V defined in equation (1). As expected, the peaks in conductance occur at voltages

$$V = \frac{2\Delta}{ne}, \quad (2)$$

where n is an integer and $\Delta = 85$ μeV (device A; 95 μeV , device B), which is close to the typical value of the superconducting gap in nanotubes contacted with a thin film of aluminium [1, 8]. Here, the superconducting gap is reduced compared to Al alone, which is due to the Pd used in the contacts. The voltages calculated from equation (2) are marked by dashed lines in figure 2(c) and align with features of low resistance as expected. For $I \gg I_c$ the differential resistance is constant, indicating the normal state resistance R_n of the supercurrent transistor. Assuming a single-walled carbon nanotube with 4 conduction channels of equal transmission, R_n can be used to calculate the transmission coefficient T via $R_n = h/(4e^2 T)$. Averaging over the full gate voltage interval shown in figure 2(a) yields $T = 0.65 \pm 0.19$. However, one should note that the lateral gate also tunes the tunnelling barrier between the contact and the carbon nanotube and hence also parameter T , as can be seen by the variations in differential resistance in figure 2(a) for $I \gg I_c$. Nevertheless, this again demonstrates the high quality contact provided by the Pd/Al bilayer.

Inspection of figure 2(a) also shows weak differential resistance even below the critical current threshold (i.e. for $|I| < I_c$). Figure 2(d) is an expanded view showing this effect. Two dotted lines highlight the resistance threshold at $I = I_c$ and this weak sub-threshold feature. Such a sub-threshold resistance indicates excitation away from the superconducting ground state. Two possible causes are thermal phase diffusion and formation of a phase slip [31]. Thermally activated phase diffusion should lead to a smoothly increasing $\partial V/\partial I$ [32], and phase slips should lead to a series of abrupt steps in V [31]. The sub-threshold feature in figure 2 does not follow either of these expectations. This is confirmed by figures 2(e) and (f), which plot V and $\partial V/\partial I$ along a single cross-section in bias current. We therefore tentatively suggest that the sub-threshold peak in $\partial V/\partial I$ indicates that the device contains two weak links in series, and that the sub-threshold peak occurs when the weaker of the two becomes normal. This might happen if the interface on one side of the device is less clean than on the other. If this is the correct explanation, then the value of I_c plotted in figure 2(c) is the critical current of the stronger link. This sub-threshold peak is not observed in device B (see below). However, we

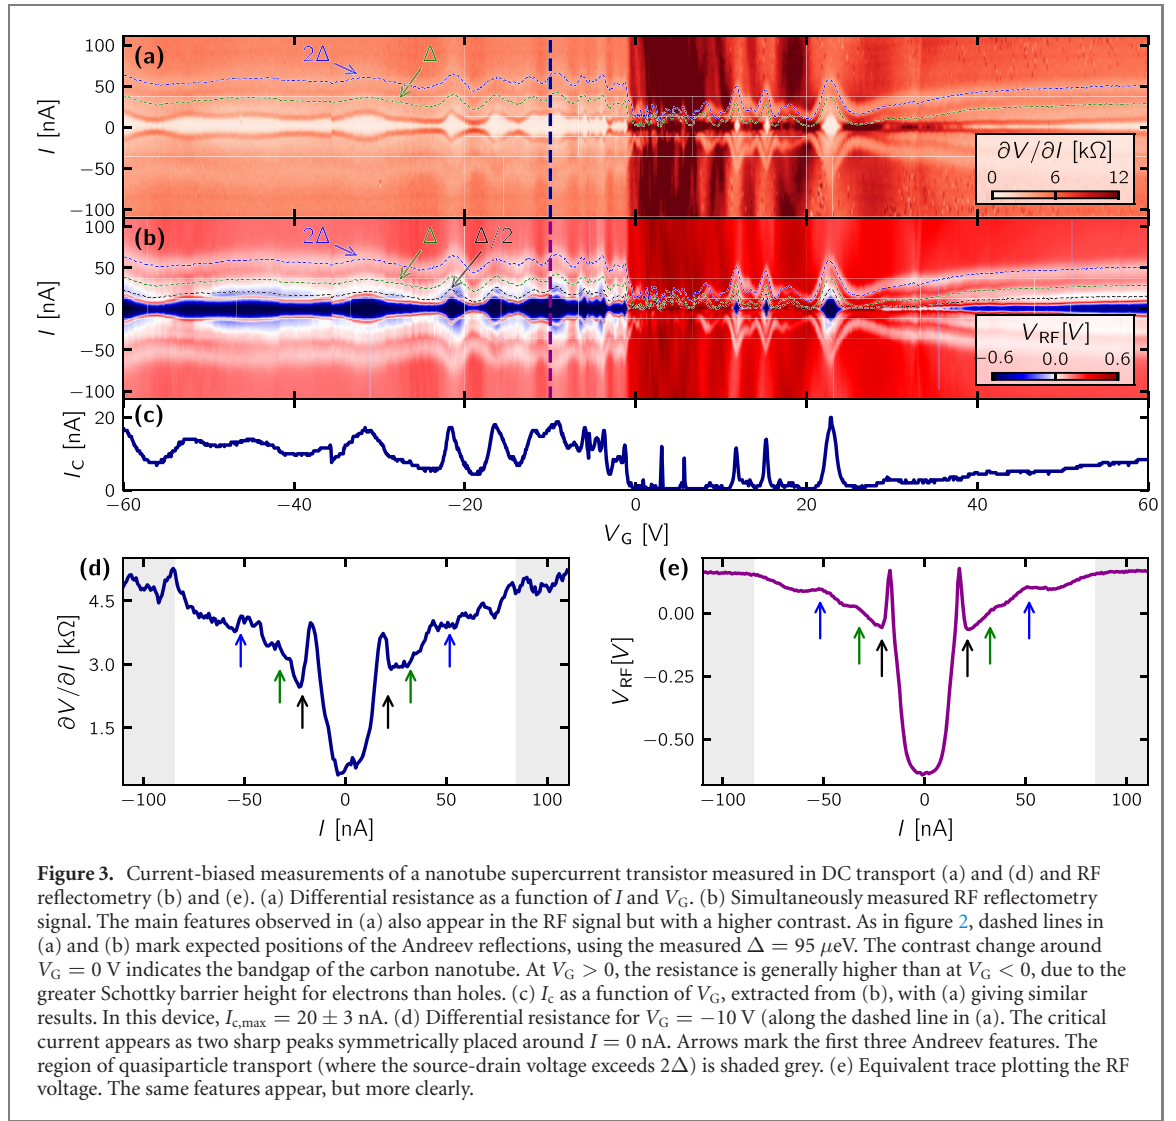

note that a similar peak has been seen just below the transition temperature in a NbN nanowire device that also exhibited thermal and quantum phase slips [33].

4. Spectroscopy using RF reflectometry

Reflectometry experiments were performed on a second device (device B) fabricated by a similar method as device A but in a separate fabrication run. Device B was bonded to the sample board in the same way as device A (figure 1) but now with the tank circuit connected. The measurement method of figure 2(a) was now repeated on device B, except that as well as the DC conductance $\partial V/\partial I$, the demodulated RF voltage V_{RF} was measured simultaneously. The integration time per point was the same for the two data sets.

Figures 3(a)–(c) show the results. As expected, the DC behaviour (figure 3(a)) is similar to the measurement presented in figure 2(a), which confirms that the supercurrent transistor can operate with an RF excitation applied. All the main features are reproduced in the RF measurement (figure 3(b)), especially the sharp change at the critical current. We find that V_{RF} is approximately proportional to the DC resistance, showing that the RF measurement successfully transduces changes in the device impedance into changes in the tank circuit's reflectance.

Some features of the DC resistance appear more clearly in the RF data, in particular the sharp superconducting transition. To explore this more thoroughly, figures 3(d) and (e) compare cross-sections at constant $V_G = -10 \text{ V}$, which is a typical gate voltage in the transistor's 'on' configuration. The superconducting transition and the first two Andreev features are evident in the conductance data (figure 3(d)) but much clearer in the reflectometry data (figure 3(e)). The signal-to-noise ratio is higher for the RF measurement. Quantifying the noise as the scatter of the data points in the quasiparticle transport regime, and the signal as the full vertical range of the traces in figure 3, the RF measurement yields an improvement of $\sim 16 \text{ dB}$. This illustrates

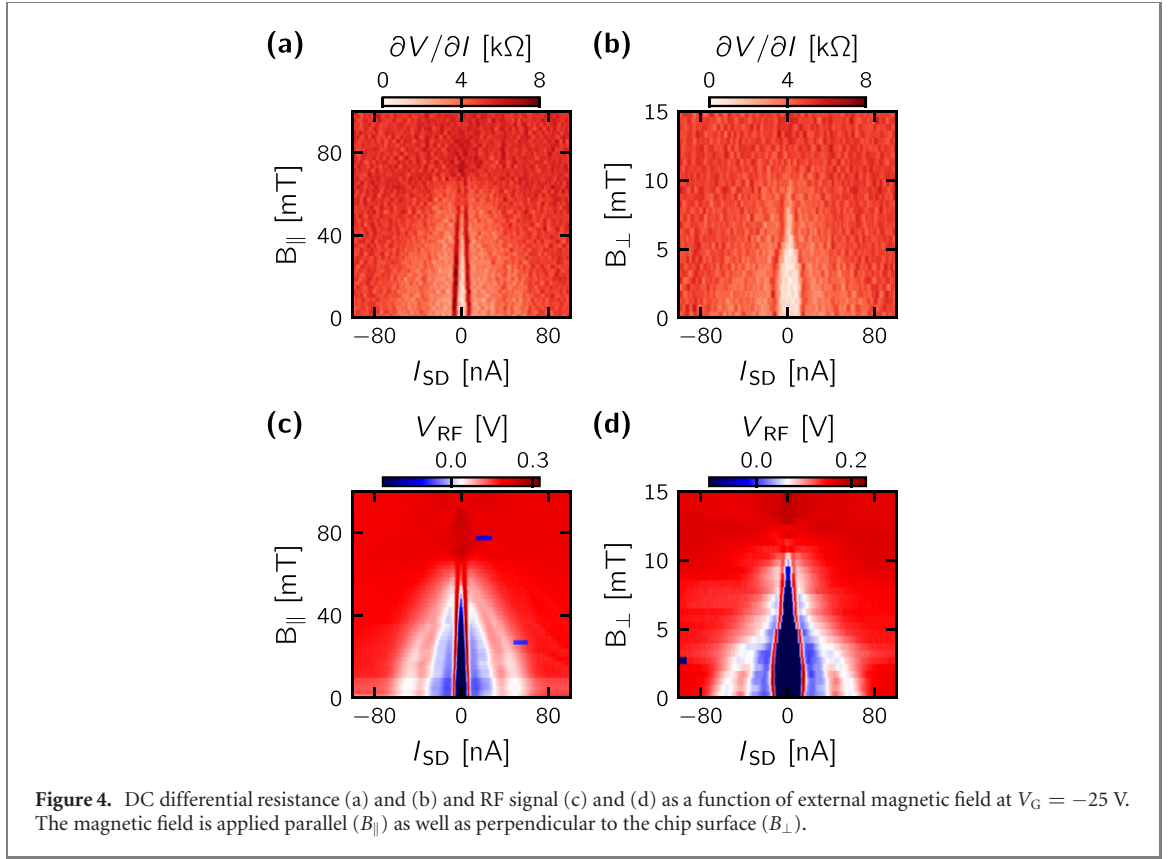


Figure 4. DC differential resistance (a) and (b) and RF signal (c) and (d) as a function of external magnetic field at $V_G = -25$ V. The magnetic field is applied parallel ($B_{||}$) as well as perpendicular to the chip surface (B_{\perp}).

the advantage of measuring at an RF frequency where $1/f$ noise is reduced compared with DC. It may also indicate that part of the RF signal is a response to the changing superconducting inductance, to which the DC measurement is insensitive.

As a further illustration of the sensitivity of RF measurement, figure 4 shows the DC differential resistance and the RF signal as a function of magnetic field applied in ($B_{||}$) and out of plane (B_{\perp}) of the device substrate. As expected, the critical current decreases with increasing field, an effect that is seen more clearly in the RF than in the DC measurement. From figure 4 a rough estimate of the perpendicular and parallel critical magnetic fields of the Pd/Al bilayer can be extracted, giving $B_{\perp,c} \sim 10$ mT and $B_{||,c} \sim 60$ mT respectively. This compares as expected with the critical magnetic field of bulk Al ($B_c \sim 10$ mT), where the B_c can be improved by aligning a thin film parallel to the magnetic field [37].

5. Conclusion

By comparing simultaneous RF and DC transport measurements of a carbon nanotube supercurrent transistor, this experiment shows that RF reflectometry is sensitive to all the main transport features, most of which appear more distinctly than in DC transport alone. Importantly, the properties of a supercurrent transistor device integrated into an RF measurement circuit are essentially identical to those of a device measured by DC transport alone. Our results show that RF reflectometry is a non-invasive technique for characterising supercurrent transistors and potentially many other nanoscale devices and physical effects. Although not tested here, reflectometry measurements can often be much faster than transport alone, and thus may allow many devices to be tested quickly under a wide range of operating conditions. Additionally, the reflectometry circuit can be placed off chip and simply connected with a bond-wire reducing device and fabrication complexity, which is a benefit of the method presented here compared to embedding the Josephson junction with DC access into a gatemon qubit [15]. This would allow, for example, rapid fluctuations of the critical current to be measured in real time [34]. The reflectometry circuit used here might also allow for fast transport characterisation of other kinds of superconducting hybrid devices, for example to compare different ways of optimising superconductor–semiconductor interfaces, which are crucial for such devices. The ability to distinguish reactive and resistive impedance changes is a possible tool for studying novel hybrid devices such as those used to realise Majorana qubits [35, 36].

Acknowledgments

We acknowledge support from the Royal Academy of Engineering, EPSRC (EP/R029229/1), the ERC (818751), the Swiss Nanoscience Institute (SNI) and the Swiss National Science Foundation. MM acknowledges support from the Stiftung der Deutschen Wirtschaft (sdw). We thank Yu A Pashkin for discussions.

Data availability statement

The data that support the findings of this study are available upon reasonable request from the authors.

ORCID iDs

M Mergenthaler  <https://orcid.org/0000-0001-5072-3037>

F J Schupp  <https://orcid.org/0000-0002-1246-8677>

N Ares  <https://orcid.org/0000-0003-2588-6322>

A Baumgartner  <https://orcid.org/0000-0003-4681-4926>

C Schönenberger  <https://orcid.org/0000-0002-5652-460X>

G A D Briggs  <https://orcid.org/0000-0003-1950-2097>

P J Leek  <https://orcid.org/0000-0002-1410-5642>

E A Laird  <https://orcid.org/0000-0001-9589-127X>

References

- [1] Jarillo-Herrero P, van Dam J A and Kouwenhoven L P 2006 *Nature* **439** 953
- [2] Cleuziou J-P, Wernsdorfer W, Bouchiat V, Ondarçuhu T and Monthieux M 2006 *Nat. Nanotechnol.* **1** 53
- [3] Larsen T W, Petersson K D, Kuemmeth F, Jespersen T S, Krogstrup P, Nygård J and Marcus C M 2015 *Phys. Rev. Lett.* **115** 127001
- [4] de Lange G, van Heck B, Bruno A, van Woerkom D J, Geresdi A, Plissard S R, Bakkers E P A M, Akhmerov A R and DiCarlo L 2015 *Phys. Rev. Lett.* **115** 127002
- [5] Delagrèe R, Weil R, Kasumov A, Ferrier M, Bouchiat H and Deblock R 2016 *Phys. Rev. B* **93** 195437
- [6] Szombati D B, Nadj-Perge S, Car D, Plissard S R, Bakkers E P A M and Kouwenhoven L P 2016 *Nat. Phys.* **12** 568
- [7] Estrada Saldaña J C, Žitko R, Cleuziou J P, Lee E J H, Zannier V, Ercolani D, Sorba L, Aguado R and De Franceschi S 2019 *Sci. Adv.* **5** eaav1235
- [8] Buitelaar M R, Belzig W, Nussbaumer T, Babić B, Bruder C and Schönenberger C 2003 *Phys. Rev. Lett.* **91** 057005
- [9] Petersson K D, Smith C G, Anderson D, Atkinson P, Jones G A C and Ritchie D A 2010 *Nano Lett.* **10** 2789
- [10] Baumgartner C, Fuchs L, Frész L, Reinhardt S, Gronin S, Gardner G C, Manfra M J, Paradiso N and Strunk C 2020 *Phys. Rev. Lett.* **126** 037001
- [11] Pei F 2014 Quantum transport in one-dimensional nanostructures *PhD Thesis* TU Delft
- [12] Hays M, de Lange G, Serniak K, van Woerkom D, Bouman D, Krogstrup P, Nygård J, Geresdi A and Devoret M 2018 *Phys. Rev. Lett.* **121** 047001
- [13] Tosi L, Metzger C, Goffman M F, Urbina C, Pothier H, Park S, Yeyati A L, Nygård J and Krogstrup P 2019 *Phys. Rev. X* **9** 011010
- [14] Murani A, Dassonneville B, Kasumov A, Basset J, Ferrier M, Deblock R, Guéron S and Bouchiat H 2019 *Phys. Rev. Lett.* **122** 076802
- [15] Kringhøj A et al 2020 *Phys. Rev. Lett.* **124** 056801
- [16] Li X, Tu X, Zaric S, Welsher K, Seo W S, Zhao W and Dai H 2007 *J. Am. Chem. Soc.* **129** 15770
- [17] Samm J, Gramich J, Baumgartner A, Weiss M and Schönenberger C 2014 *J. Appl. Phys.* **115** 174309
- [18] Ares N et al 2016 *Phys. Rev. Appl.* **5** 034011
- [19] Schupp F J et al 2020 *J. Appl. Phys.* **127** 244503
- [20] Mueller F, Schouten R N, Brauns M, Gang T, Lim W H, Lai N S, Dzurak A S, van der Wiel W G and Zwanenburg F A 2013 *Rev. Sci. Instrum.* **84** 044706
- [21] Roschier L, Sillanpää M, Taihong W, Ahlskog M, Iijima S and Hakonen P 2004 *J. Low Temp. Phys.* **136** 465
- [22] Biercuk M J, Reilly D J, Buehler T M, Chan V C, Chow J M, Clark R G and Marcus C M 2006 *Phys. Rev. B* **73** 201402
- [23] Delbecq M R et al 2011 *Phys. Rev. Lett.* **107** 256804
- [24] Chorley S J, Wabnig J, Penfold-Fitch Z V, Petersson K D, Frake J, Smith C G and Buitelaar M R 2012 *Phys. Rev. Lett.* **108** 036802
- [25] Ranjan V, Puebla-Hellmann G, Jung M, Hasler T, Nunnenkamp A, Muoth M, Hierold C, Wallraff A and Schönenberger C 2015 *Nat. Commun.* **6** 7165
- [26] Chen Z, Appenzeller J, Knoch J, Lin Y-m and Avouris P 2005 *Nano Lett.* **5** 1497
- [27] Schneider B H, Etaki S, van der Zant H S J and Steele G A 2012 *Sci. Rep.* **2** 599
- [28] Pallecchi E, Gaaß M, Ryndyk D A and Strunk C 2008 *Appl. Phys. Lett.* **93** 072501
- [29] Mergenthaler M, Nersisyan A, Patterson A, Esposito M, Baumgartner A, Schönenberger C, Briggs G A D, Laird E A and Leek P J 2021 Circuit quantum electrodynamics with carbon-nanotube-based superconducting quantum circuits *Phys. Rev. Applied* **15** 064050
- [30] Nazarov Y V and Blanter Y M 2009 *Quantum Transport: Introduction to Nanoscience* (Cambridge: Cambridge University Press)
- [31] Tinkham M 1996 *Introduction to Superconductivity* 2nd edn (New York: McGraw-Hill)
- [32] Ambegaokar V and Halperin B I 1969 *Phys. Rev. Lett.* **22** 1364
- [33] Masuda K, Moriyama S, Morita Y, Komatsu K, Takagi T, Hashimoto T, Miki N, Tanabe T and Maki H 2016 *Appl. Phys. Lett.* **108** 222601
- [34] Rogers C and Buhrman R 1983 *IEEE Trans. Magn.* **19** 453
- [35] Aguado R and Kouwenhoven L P 2020 *Phys. Today* **73** 44

- [36] Smith T B, Cassidy M C, Reilly D J, Bartlett S D and Grimsmo A L 2020 *PRX Quantum* **1** 020313
- [37] Kroll J *et al* 2019 *Phys. Rev. Appl.* **11** 064053