The Electrochemical
Society Interface

FEATURED ARTICLES

Electrolysis in Chloride Molten Salts for Sustainable Critical Metals Production and Recovery

To cite this article: Ben Holcombe *et al* 2024 *Electrochem. Soc. Interface* **33** 49

View the article online for updates and enhancements.

You may also like

- Alkali Chloride Molten Salt Corrosion Testing Using a Rotating Cylindrical Electrode
Ty Townsend and Dev Chidambaram
- Selection About Molten Salts Used For The Electrochemical Reduction of Porous TiO_2 pellets
Kejia Liu, Yaowu Wang, Yuezhong Di et al.
- Online Monitoring of Alkali Chloride Molten Salt Composition, Speciation, and Basicity Using UV-Vis-NIR Absorption Spectroscopy
Jeremy Moon, Laurel Sharpless and Dev Chidambaram

Enabling Electrochemistry Inside and Outside the Lab

PalmSens

Discover our diverse range of Potentiostats engineered to support your research wherever it takes you

- Intuitive software for Windows and Android
- Proven in over 4000 scientific publications
- Single-channel and multi-channel
- Benchtop, portable and wearable

Discover More



This content was downloaded from IP address 216.73.216.56 on 19/11/2026 at 09:36

Electrolysis in Chloride Molten Salts for Sustainable Critical Metals Production and Recovery

by Ben Holcombe, Nicholas Sinclair, Alexander Baker, Eunjeong Kim, Scott K. McCall, and Rohan Akolkar

Oxy–fluoride vs. Chloride Molten Salt Electrolysis

Rare-earth elements (REEs) are "critical" materials for many existing and emerging technologies. Electrified transportation, wind power generation, magnetic data storage, and even defense equipment rely on neodymium (Nd), praseodymium (Pr), and dysprosium (Dy) as key components of permanent magnets that enable these technologies. Demand for REEs has drastically increased over the past few decades and is predicted to continue to grow even further. Currently, the processing and refining of REEs involve environmentally hazardous and energy–intensive steps that restrict their practice primarily to countries with less stringent environmental regulations. But heavy dependence on a single source for critical materials access poses serious supply chain risks. Developing innovative yet sustainable methods for refining critical metals is crucial for mitigating the environmental impacts caused by currently practiced REE processing methods.[1]

REE production involves many steps (i.e., mining, ore beneficiation, solvent extraction, and purification) as shown in Fig. 1. These steps yield rare-earth oxides, which are converted into metal via electrolysis. Here, we focus on neodymium (Nd) metal production, although the overall approach to metal production is similar for other rare-earths. The state-of-the-art process for Nd production uses a Nd_2O_3-containing NdF_3-LiF molten salt electrolyte (at temperatures exceeding 1050 °C) and a consumable carbon anode.[2] This oxy–fluoride process converts purified Nd_2O_3 and the carbon to Nd metal (at the cathode) and generates CO_2 (at the anode). See Fig. 1. However, the low solubility of Nd_2O_3 implies transport limitations on oxygen species at the anode, resulting in an appreciable amount of perfluorocarbon (PFC) gas emissions in addition to CO_2. These greenhouse gases (CO_2, PFCs) make the conventional oxy–fluoride molten salt electrolysis (MSE) process undesirable. Additionally, the consumable carbon anode necessitates a "batch" process, requiring frequent heating and cooling cycles, rendering it very energy intensive (>8 kWh/kg, accounting for all energy inputs).[3] Despite these disadvantages, the state-of-the-art molten salt electrolysis (MSE) process does present some key advantages: molten salts offer excellent ionic conductivities and high diffusivities, and high-temperature operation provides fast reaction kinetics—these are essential features for process scale-up, for lowering overpotentials and energy consumption, and for achieving high electrolysis rates.[2,4]

Moderate- or high-temperature chloride–based molten salts present an alternative medium to conventional oxy-fluoride melts because they also possess exceptional transport and kinetics properties, while allowing for more energy-efficient and sustainable metal refining.[4] A comparison between the chloride-based MSE process and the state-of-the-art oxy-fluoride process is depicted in Fig 1. In the chloride MSE route, Nd_2O_3 is first converted into $NdCl_3$ via noncarbothermic reaction with HCl or Cl_2 gas. This process is uniquely possible for rare-earths because their chlorides are more thermodynamically stable than their oxides.[2] The resulting chloride salt is then used as a feedstock for molten salt electrolysis. The medium for electrolysis can be a variety of chloride eutectic melts (e.g., LiCl-KCl in a 59:41 mole % ratio), which are readily available, benign, and provide a wide electrochemical potential operating window for electrolysis.[4] When operated at moderate temperatures, electrolysis yields solid Nd metal. The Cl_2 gas emitted at the anode can be sold—as it is a valuable co-product—or it can be recycled into the upstream chlorination step. This process offers numerous advantages over the conventional route: (i) First and foremost, the chloride MSE route does not generate direct greenhouse gas (CO_2, PFCs) emissions, and thus is fully sustainable. (ii) Cl_2 evolution offers the possibility of using a dimensionally stable, catalytic anode which not only lowers anode overpotentials and thus the cell voltage and energy consumption, but also provides better process control, including continuous processing.[5-7] (iii) Reactor design and electrolyte optimization can enable higher current efficiencies (>80%), thus enhancing overall process efficiency above and beyond the conventional oxy-fluoride process. These aspects are discussed in further detail below.

Specific energy consumption (i.e., the amount of energy required to produce a given mass of Nd metal, kWh/kg-Nd), is a metric that considers thermodynamics and overvoltage penalties associated with the irreversibility factor during electrolysis, as well as inefficiencies from parasitic side reactions.[2] For the chloride MSE process, the thermodynamic potential for electrolysis of $NdCl_3$ (2.7 V) is higher than the oxy-fluoride process because $NdCl_3$ is more stable than Nd_2O_3. However, the chloride MSE process has significantly lower electrolyte resistance, improved species transport, and potentially offers fast kinetics at both the anode and the cathode. These characteristics

(continued on next page)

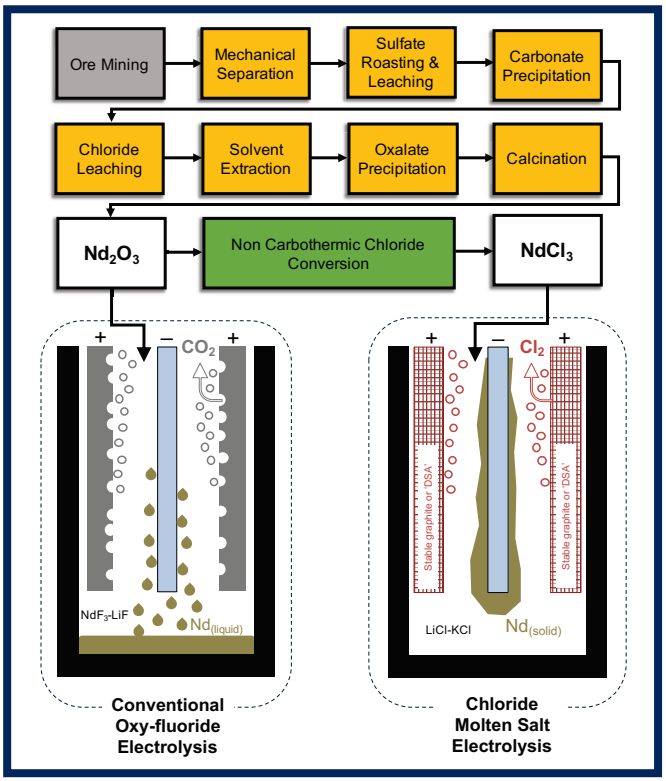


Fig. 1. *A process flow diagram and associated reactor schematics for both the conventional oxy-fluoride process and an alternative chloride-based electrolysis process. While the chloride process requires first converting Nd_2O_3 to $NdCl_3$, it offers the benefits of eliminating CO_2 and PFC emissions, improved process control due to a more stable inter-electrode spacing provided by the nonconsumable nature of the anode, and improved energy efficiency on account of the higher current efficiency and lower cell voltage when using a catalytic DSA anode.*

(continued from previous page)

Table I. Comparison of key process metrics between conventional oxy-fluoride electrolysis and the chloride MSE alternative for Nd metal production.

PROCESS METRIC	OXY-FLUORIDE MSE	CHLORIDE MSE
Thermodynamic Potential	2.5 V	2.7 V
Cell Voltage	4.0 V	< 4.0 V
Coulombic Efficiency	< 60%	> 80%
Specific Energy (kWh/kg)	8.0*	< 2.79
Direct CO_2 emissions	0.2 kg-CO_2 / kg-Nd	none

**electrical energy consumption is 3.7 kWh/kg; however, the need for heating batch reactors elevates the net energy consumption for the oxy-fluoride process. Chloride MSE opens up avenues for continuous processing, which could eliminate heating costs.*

allow the chloride process to operate at cell voltages that are at parity with or lower than the oxy-fluoride process. Considering the higher cathodic coulombic efficiency (discussed below) in chloride MSE, this process can enable much lower specific energies, thus creating a more sustainable process by lowering the energy consumed as well as by eliminating direct greenhouse gas production.[2] A comparison of the relevant process parameters is provided in Table I.

Molten Salt Electrolysis in Chloride Melts – Fundamental and Practical Considerations

There are a few key considerations in designing efficient rare-earth electrowinning processes, especially as they relate to chloride MSE. A key aspect of process design in MSE of rare-earths, including Nd, is their multivalency (i.e., stability of multiple oxidation states in a halide medium). For Nd, Nd^{3+} and Nd^{2+} are both stable.[4] Thus, during electrolysis, $NdCl_3$ is first converted to Nd^{2+} (very fast step [1] shown in Fig. 2), followed by reduction of Nd^{2+} to Nd metal (relatively slow step [2] in Fig. 2). Nd^{2+} is susceptible to diffusion away from the cathode, which represents an efficiency loss. To quantify this loss, an efficiency loss factor $\mathcal{L}$ may be defined as the ratio of the rate of Nd^{2+} loss through diffusion to the rate of Nd^{2+} reduction to metal. As shown in Fig. 2 (right), $\mathcal{L}$ is proportional to the Nd^{2+} diffusion–limited mass transfer coefficient ($\mathcal{D}_{2+}/\delta$) and its concentration (C_{2+}), and inversely propositional to the exchange current density (i_0) and overpotential (η) for Nd deposition. Thus, to minimize Nd^{2+} loss, the electrolysis process must be operated at very large overpotentials (as large as possible without triggering parasitic reactions such as LiCl or KCl electrolysis)–this ensures fast reduction of Nd^{2+} to metal, thereby preventing Nd^{2+} loss to the electrolyte. Also, strategies to employ porous separators or diffusion barriers are effective in preserving the Nd^{2+} near the cathode and avoiding Nd^{2+} oxidation back to Nd^{3+} at the anode. Finally, temperature has a key role to play, since increasing temperature increases i_0 and thus lowers the loss factor.

Electrowinning of solid Nd sponge at the cathode is advantageous because, unlike conventional oxy-fluoride processing, the product Nd stays adhered to the cathode surface and thus continually experiences an externally imposed cathodic potential. This avoids the possibility of a spontaneous comproportionation reaction between Nd and the electrolyte via: $Nd + Nd^{3+} \rightarrow 2Nd^{2+}$. This reaction is thermodynamically favored[4] when an externally unpolarized Nd droplet contacts the electrolyte, as is the case in the oxy-fluoride process (Fig. 1). However, producing solid Nd via chloride MSE comes with its own set of challenges. Because metal deposition in moderate- and high-temperature melts takes advantage of the intrinsically high exchange current densities in these media, spongy or porous deposits are typically obtained.[2] As shown in Fig. 3, high purity (spot purity >92 at.%) deposits are easily obtained via chloride MSE; however, FIB-liftout followed by SEM/EDS reveals porosity in the deposited Nd metal. Electrolyte salts (e.g., LiCl and KCl) become entrapped in the Nd pores during electrolysis. This necessitates postprocessing such as vacuum distillation or arc remelting to purify the Nd so that it is suitable for application in NdFeB permanent–magnet fabrication. Recent developments in the use of electrolyte additives are noteworthy in this context.[8] Additives can enable more compact and thus ultra-high-purity electrowon metal that circumvents the need for postpurification, thereby maintaining the energy requirements at a minimal value during metalmaking.

To circumvent efficiency loss due to multivalency, and to mitigate salt entrapment when making solid Nd metal, higher temperature (>860 °C) chloride MSE may be practiced. Several chloride mixtures (e.g., $BaCl_2$–KCl above 650 °C) are stable liquids at very high temperatures. When electrolysis is performed in such melts containing $NdCl_3$ (≈2.4 M) at 860 °C, solid Nd is produced, as evidenced in the CV in Fig. 4. Here, the negative scan direction yields Nd electrodeposition at cathodic potentials, but the reverse scan (going toward positive potentials from –2.0 V to –0.4 V vs. Mo quasi-reference electrode) exhibits Nd stripping because the solid Nd product is adhered to the tungsten (W) working electrode. Electrolysis at even higher temperatures (1050 °C, i.e., above the Nd melting point) also yields Nd plating as expected, but the stripping peak during the reverse scan is largely absent. This indicates that liquid Nd formed during the negative scan does not adhere to the cathode surface

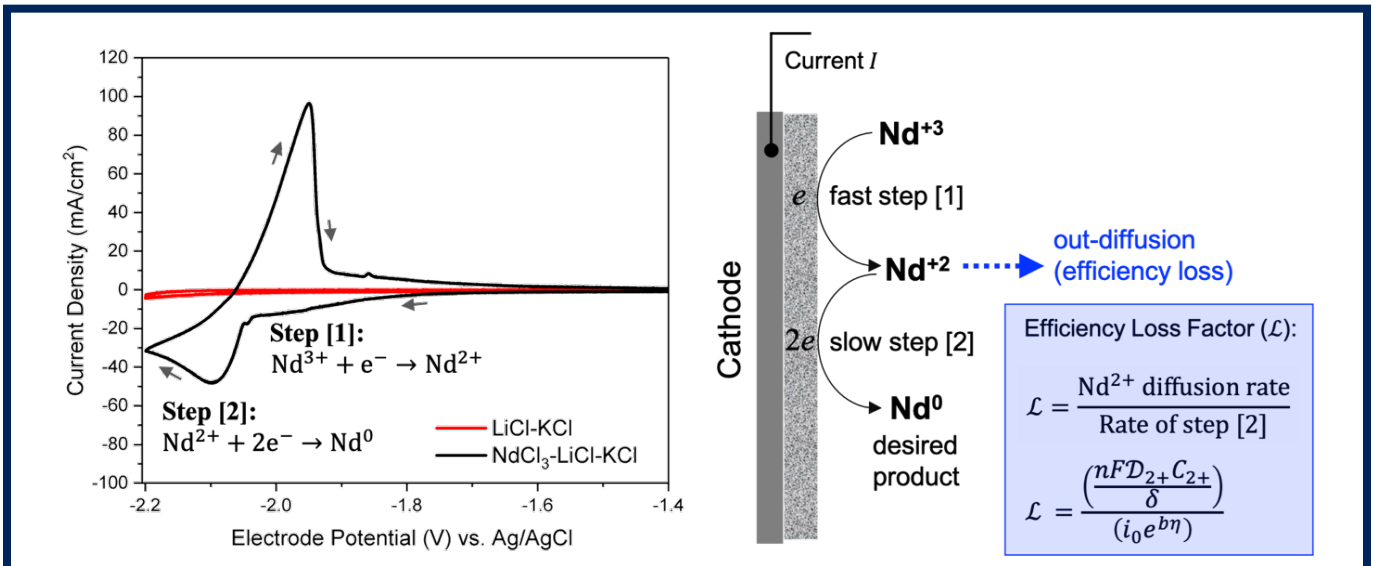


Fig. 2. *(left) Cyclic voltammogram (CV, at 100 mV/s) gathered on a tungsten working electrode immersed in molten LiCl-KCl eutectic electrolyte at 475 °C in the presence (black curve) and in the absence (red curve) of $NdCl_3$.[4] CV shows reduction of $NdCl_3$, first from Nd^{3+} to Nd^{2+}, followed by reduction to Nd^0 (metal). (right) The intermediate Nd^{2+} is prone to out-diffusion, which contributes to efficiency loss. Efficiency loss can be minimized by lowering the loss factor $\mathcal{L}$, which is defined as the ratio of the Nd^{2+} diffusion rate to the Nd deposition rate via step [2].*

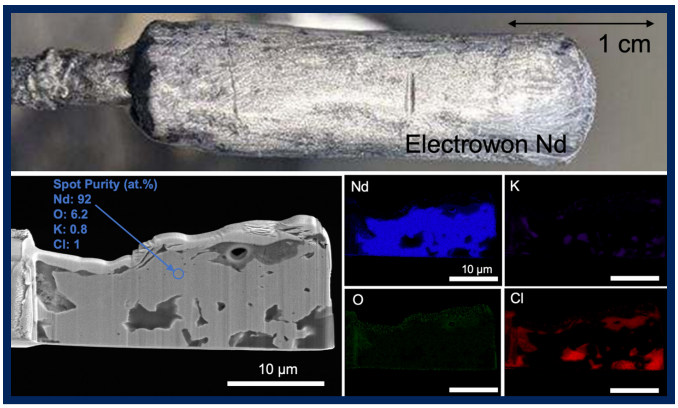


Fig. 3. *A Nd deposit produced by electrolysis at 200 mA/cm² in a 1.65 M $NdCl_3$ containing LiCl-KCl electrolyte at 500 °C (top). FIB liftout followed by SEM/EDS shows high purity (92 at.%) Nd regions but also shows entrapped salt (likely LiCl) due to the porous nature of the Nd deposits.*

because liquid Nd (density = 6.9 g/cm³) settles at the bottom of the electrolyte (density ≤ 3 g/cm³) and thus is detached from the working electrode. This experiment suggests the possibility of electrowinning liquid Nd metal, as has been explored recently by several other investigators.[9] Liquid metal plating exhibits very high exchange current densities (≈1–10 A/cm²) compared to solid metal plating (0.1 A/cm²),[10] thus liquid Nd plating can lower the efficiency loss factor f_c (Fig. 2) as long as comproportionation-related losses can also be minimized. Finally, liquid metal plating opens the possibility for a truly "continuous" process in which metal is continually electrowon and separated—this route is attractive for scale-up, process control, and overall process technoeconomics.

Challenges and Prospects for Future Development of Chloride MSE

While the chloride-based MSE route is a promising method for enabling clean and sustainable rare-earth metal production across the globe, there remain several unresolved challenges. Chlorine handling, particularly at high temperatures, is a key safety concern. High-temperature chlorine corrosion is more aggressive, due not only to the increased rate of transport of chlorine through passivating surface oxide films, but also to the volatility of metallic chlorides.[11] While enhanced chlorine corrosion poses a materials challenge for chlorine-handling systems, it also restricts the usability of traditional anode materials. Conventional titanium-coated mixed metal oxide (MMO) dimensionally stable anodes (DSAs) are common in lower temperature aqueous chlor-alkali processes; however, the sintered oxide coating can delaminate from the titanium substrate, presumably due to chlorine penetration leading up to corrosive attack of the underlying titanium during high-temperature chloride MSE. Graphite itself can act as a chlorine-evolving anode, but it typically exhibits larger overpotentials for chlorine evolution than MMO and can itself oxidize to CO_2 in the presence of trace water or oxygen during chloride MSE. New DSA materials or stacks need to be developed to address these issues of long-term anode stability while also lowering the anodic overpotentials during chloride MSE.[12]

Despite the many advantages of the moderate-temperature chloride MSE process, it remains a "batch" process around 500 °C. The electrowon solid Nd needs to be collected by removing the cathode from the electrolyte melt at the end of a batch. While a cathode "swap" could be performed while the cell is held at temperature to minimize process interruptions, a truly "continuous" process is very desirable for scalability, cost, and energy-efficiency. Work is underway in our laboratory to develop a novel reactor and process design to continuously electrowin liquid Nd metal at 1050 °C in a chloride melt. Using an inert yet catalytic anode material, a low volatility chloride electrolyte (e.g., $BaCl_2$–KCl or $BaCl_2$–$SrCl_2$), and a reactor design to periodically siphon the molten metal akin to industrial Al electrowinning, a continuous process is possible. A continuous process would greatly reduce the specific energy consumption by eliminating the heating-cooling cycles necessary for the conventional oxy-fluoride route.

Implementation of chloride MSE requires a $NdCl_3$ feedstock. Producing a chloride feedstock first requires Nd_2O_3 production from ore via the established methods of ore processing (Fig. 1). In ore processing, a mixed rare-earth chloride stream undergoes treatment using an organic ligand such as oxalate to selectively precipitate Nd^{3+}. The oxalate is then calcined into Nd_2O_3, which releases CO_2. Targeting this chloride intermediate stream rather than a purified oxide could provide opportunities for upstream integration of chloride MSE, which would further reduce the overall CO_2 emissions associated with primary Nd production. An even greener alternative feedstock is the large volume of used magnets in end-of-life devices such as hard disk drives and wind turbines. Additional reduction in CO_2 emissions can be achieved through recycling of the Nd in used magnets. It has been shown that oxide feedstocks derived from used magnets could provide a >50% reduction in greenhouse gas emissions compared to those produced from ore bodies.[13] Given that recycling also often involves an oxalate treatment followed by a calcination step, targeting the separation of Nd from NdFeB magnets into its chloride form ($NdCl_3$) for direct input into chloride MSE offers an opportunity to achieve nearly complete circularity in rare-earth processing.

Note here that Nd separation from NdFeB may also be achieved electrolytically in an electrorefining cell (Fig. 5) with chloride molten salt as the electrolyte. Here, Nd from NdFeB is selectively oxidized to Nd^{3+} (at the anode), which then undergoes reduction to pure Nd metal (at the cathode)—this has the potential to accomplish separation and purification in a single unit operation. Cyclic voltammetry of $NdCl_3$- and $FeCl_2$-containing melts confirms that selective separation of Nd can be achieved over a rather wide potential range (Fig. 5). However, a key challenge in realizing such separation is the slow solid-phase diffusivity of Nd out of the NdFeB anode. Utilizing micro-sized NdFeB particles with short diffusion lengths and high surface areas will be key to achieving industrially relevant rates of Nd separation and electrorefining. Specialized pulsing waveforms can be employed as well to maximize transport of Nd out of the solid particle and into Nd^{3+} species while preserving selectivity.[14]

Summary

Critical materials, such as rare-earth metals, are essential to numerous applications, including clean energy; however, the present industrial practices for producing rare-earth metals involve environmentally damaging and thus unsustainable chemical and electrochemical processes. For example, neodymium metal

(continued on next page)

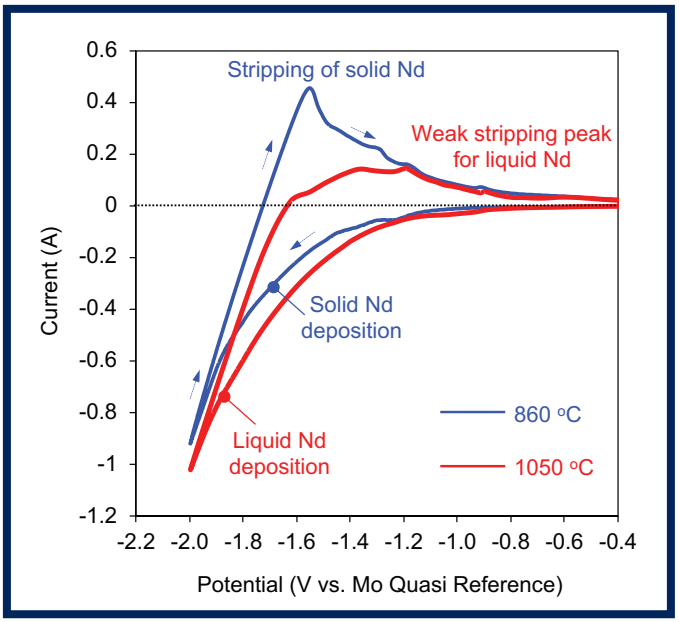


Fig. 4. *Cyclic voltammetry (200 mV/s) at a cylindrical W electrode in a $BaCl_2$–KCl molten salt containing 2.4 M $NdCl_3$. CV suggests that, at 860 °C (below the Nd metal melting point), solid Nd is formed during the cathodic scan direction. This Nd adheres to the W working electrode, and then undergoes oxidation during the reverse scan. However, at 1050 °C, liquid Nd is electrowon which separates (due to higher density than the electrolyte) from the W electrode, and thus is not re–oxidized during the reverse scan. This hints at the possibility of making liquid Nd via chloride MSE.*

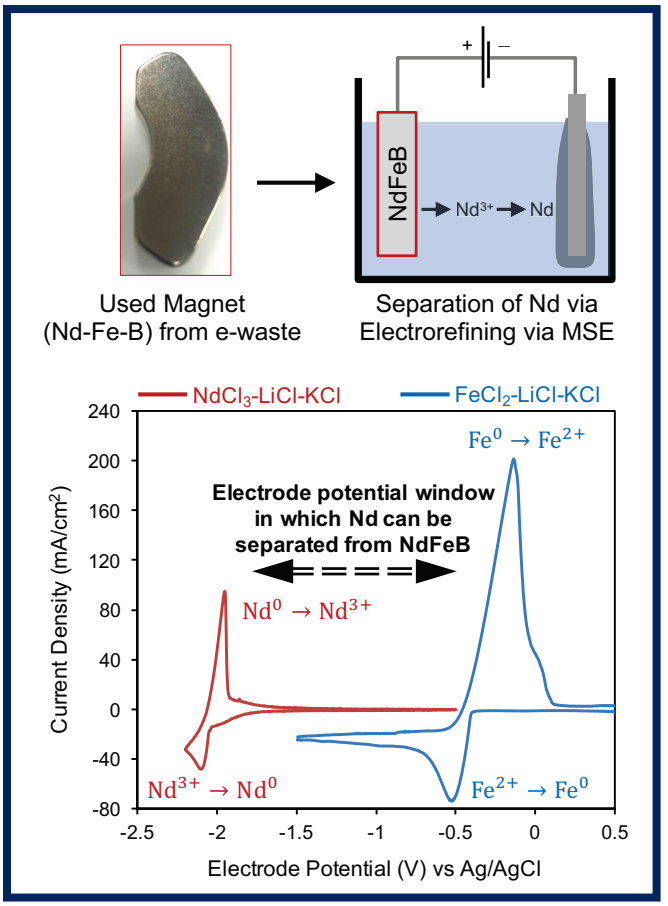


Fig. 5. *An exploratory concept for recovering Nd from used NdFeB magnets from electronic waste. Recovery is achieved via electrorefining in which Nd undergoes selective oxidation at the anode and is deposited as pure Nd metal at the cathode. Cyclic voltammetry of $NdCl_3$ and $FeCl_2$ containing LiCl-KCl melts confirms that selective Nd separation from NdFeB is feasible at anode potentials in the approximate range of –1.7 to –0.8 V vs. Ag/AgCl.*

production using oxy-fluoride molten salt electrolysis is not only energy-inefficient but also generates potent greenhouse gases (CO_2, PFCs). An alternative moderate-temperature chloride-based molten salt electrolysis process can address these issues, providing energy-efficient and sustainable neodymium metal production. But more work is needed in advancing this process: developing catalytic yet stable chlorine-evolving anodes; "continuous" metal recovery while enhancing its purity; and upstream or downstream (recycling) integration into the supply chain for minimizing greenhouse gas emissions. The chloride MSE can be viewed as a platform technology. While it is being developed presently for rare-earth electrowinning, one can easily envision its broader application to rare-earth electrorefining and the electrolytic production of high-volume metals like Fe and Al. Presently, these high-volume metals industries account for nearly 10% of global greenhouse gas emissions. Thus, the chloride MSE process presents a huge opportunity for truly achieving sustainability if it is developed further for producing Fe, Al, Ti, Mg, and other commodity metals.

Acknowledgements

The authors acknowledge support from the US Department of Energy's Office of Energy Efficiency and Renewable Energy under the Advanced Materials and Manufacturing Technologies Office, Award Number DE-EE0009434. This work was also supported by the Critical Materials Innovation Hub, an Energy Innovation Hub funded by the US Department of Energy, Office of Energy Efficiency and Renewable Energy, Advanced Manufacturing and Materials Technologies Office.

©The Electrochemical Society. DOI: 10.1149/2.F09241IF

About the Authors



Ben Holcombe, PhD Candidate, Chemical Engineering, Case Western Reserve University (CWRU) & Critical Materials Institute (CMI)
Education: BE in Chemical Engineering (CWRU)
Research Interests: Industrial electrochemistry and electrochemical engineering; Sustainable manufacturing; Electrochemical reaction engineering; Understanding and modeling of the interplay between charge and mass conservation in non-aqueous, multivalent metal electrodeposition; Developing novel electrodes and cell designs for high temperature molten salt electrolysis systems.
Honors & Awards: CWRU Monroe J. Bahnsen Award for excellence in design and undergraduate research, ACS Associate's Award for Excellence in Organic Chemistry (Trenton Region), Betty Wallace Cornelius Award for Excellence in Mathematics.
https://orcid.org/0009-0003-4501-8431



Nick Sinclair, Staff Scientist & Adjunct Instructor, CWRU
Education: PhD in Chemical Engineering (CWRU)
Research Interests: Advanced energy storage systems based on redox organics in deep eutectic solvent electrolytes
Work Experience: As a staff engineer, researched electrochemical technologies from bench-top proof-of-concept to scaled-up systems leading to successful tech-transfer to an industrial licensee of a DOE ARPA-E sponsored energy storage concept utilizing Fe electrochemistry. Experienced with electrolysis cell design and scale-up, as well as manufacturing for a variety of industrial applications. Most recently, he has been involved in the development of a molten salt electrolysis process for the sustainable production of rare-earth metals.
https://orcid.org/0000-0002-8268-966X



Alex Baker, Staff Scientist, Actinide and Lanthanide Science Group, Lawrence Livermore National Laboratory (LLNL)
Education: MPhys in Physics (University of Durham), PhD in Condensed Matter Physics (University of Oxford and Diamond Light Source)
Research Interests: Understanding the structural, chemical, mechanical, magnetic, and electronic properties of metals.
Work Experience: Worked with the Ames National Laboratory Critical Materials Institute (CMI) for 6 years, including as an LLNL lead on efforts related to maturation of new permanent magnet formulations and on Nd electrowinning.
Pubs + Patents: >60 journal publications
Honors & Awards: R&D 100 award for his work on the Al-Ce alloy which seeks to improve the economics of rare-earth mining by developing a high-volume coproduct demand.
https://orcid.org/0000-0003-0700-0858



Eunjeong Kim, Postdoctoral Researcher, Materials Science Division, Actinide and Lanthanide Science Group, LLNL
Education: PhD in Materials Science Engineering (Hanyang University).
Research Interests: Characterization of hot-deforming NdFeB, CeFeN magnets and DSA anodes for Nd electrowinning, Development of heavy-metal high-entropy alloy hohlraum materials through a sputtering deposition process.
Work Experience: Prior to joining LLNL in 2022, her doctoral research centered around investigating magnetocaloric refrigerant materials for active magnetic regeneration systems.
https://orcid.org/0009-0004-1295-1484



Scott McCall, Physicist, LLNL & Lead, Crosscutting Research, Critical Materials Institute (CMI)
Education: PhD in Condensed Matter Physics (Florida State University)
Research Interests: Understanding the structural, chemical, mechanical, magnetic, and electronic properties of lanthanides and actinides.
Work Experience: Extensive background working on critical materials topics important for the energy, economic, and national security of the United States. A founding member of CMI, he currently leads its Crosscutting Research Focus Area. He is also the Actinide & Lanthanide Science Group Leader in the Materials Science Division LLNL
Pubs + Patents: >100 papers, of which ~50 are focused on rare-earths; >12 patents on rare-earth materials.
https://orcid.org/0000-0002-7979-4944



Rohan Akolkar, Milton and Tamar Maltz Professor of Energy Innovation, CWRU
Research Interests: Span many areas of electrochemical engineering, including batteries, semiconductors, and electrometallurgy.
Work Experience: An Ohio Eminent Scholar, Faculty Director of CWRU's Great Lakes Energy Institute, Director of the CWRU Electronic Design Center (EDC), and Chief Scientist at the Pacific Northwest National Laboratory. Prior to joining the CWRU faculty in 2012, he conducted R&D at Components Research Division of Intel Corporation.
Honors & Awards: 2023 Electrodeposition Division Research Award of ECS, Norman Hackerman Young Author Award of ECS, and recent election as Senior Member of the National Academy of Inventors (NAI).
Work with ECS: Associate Editor of the *Journal of the Electrochemical Society*.
https://orcid.org/0000-0002-9865-5704

References

1. B. J. Smith, M. E. Riddle, M. R. Earlam, C. Iloeje, and D. Diamond, *Rare Earth Permanent Magnets: Supply Chain Deep Dive Assessment*. (United States, 2022).
2. R. Akolkar, *J Electrochem Soc*, **169**, 043501 (2022).
3. A. Schreiber, J. Marx, P. Zapp, and W. Kuckshinrichs, *Adv Eng Mat*, **22**, 1901206 (2020).
4. D. Shen and R. Akolkar, *J Electrochem Soc*, **164**, H5292-H5298 (2017).
5. R. Akolkar, *System and process for sustainable electrowinning of metal*. US Patent application 2023/0279572 A1 (2023).
6. M. F. Chambers and J. E. Murphy, Molten-Salt Electrolysis of Neodymium from a Chloride Electrolyte. *Report of Investigations 9391*, US Bureau of Mines (1991).
7. N. S. Sinclair, D. R. N. Wasalathanthri, B. Mainali, B. Holcombe, A. Orhan, and R. Akolkar, *ECS Meeting Abstracts,* MA2022-02, 2500 (2022).
8. S. A. Kuznetsov, A. V. Popova, Y. V. Stulov, and S. I. Markovich, *J Electrochem Soc*, **170** 076508 (2023).
9. D. K. Sahoo, PhD Thesis, "Study on Electrodeposition of Light Rare Earth Metals and Alloys from Molten Chloride Electrolytes," Homi Bhabha National Institute (2015).
10. J. Thonstad and S. Rolseth, *Electrochmica Acta,* **23**, 223 (1978).
11. W. Zhai, B. Yang, S. Zhang, J. Ni, S. Li, and Y. Li, *IOP Conference Series: Earth and Environmental Science,* **450**, 012006 (2020).
12. R. Akolkar, B. Holcombe, N. S. Sinclair, and D. R. N. Wasalathanthri, *Dimensionally Stable Anode for Electrolytic Chlorine Evolution in Molten Salts*. US patent application filed (2023).
13. H. Jin, P. Afiuny, T. McIntyre, Y. Yih, and J. W. Sutherland, *Procedia CIRP,* **48**, 45 (2016).
14. H.-S. Lim et al., *Report 34948*, Pacific Northwest National Laboratory, Richland WA (Sept 2023).





SAVE 20%


ON THE MOST TRUSTED RESOURCES IN ELECTROCHEMISTRY

The Electrochemical Society book series provides authoritative, detailed accounts on specific topics in electrochemistry and solid state science and technology. These titles are sponsored by ECS and published in cooperation with Wiley.


ECS members receive 20% off all Wiley books. ECS members use **promo code ECS18** at checkout.

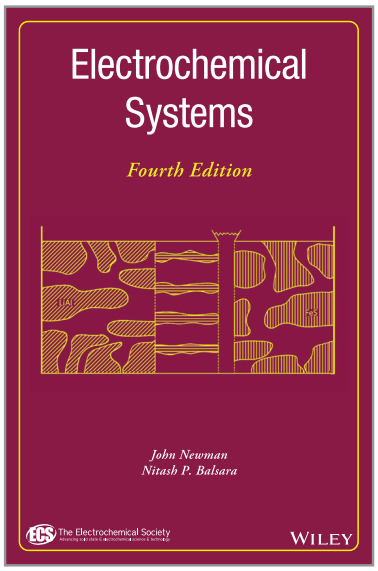

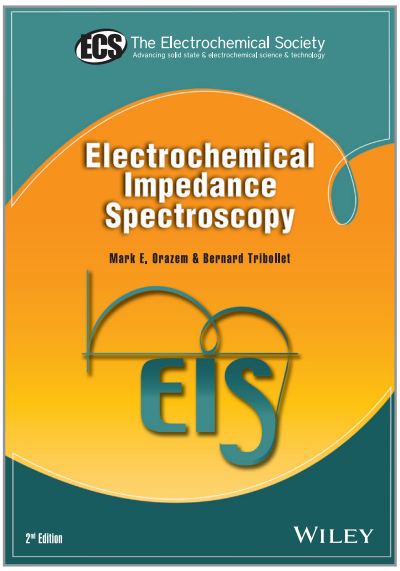

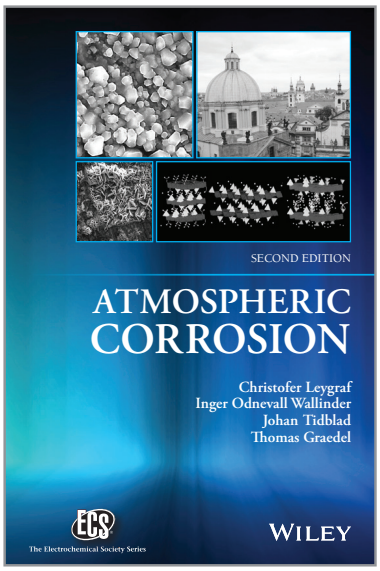

New

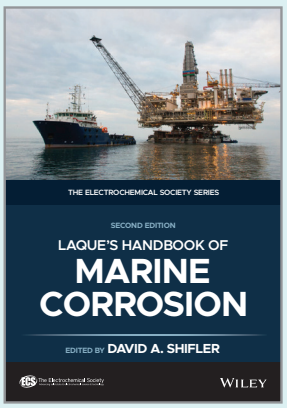

LaQue's Handbook on Marine Corrosion, 2nd Edition

David A. Shifler

ISBN 978-1-119-78883-6 | July 2022

A practical, single-source reference on the unique nature of seawater as a corrosive environment. Explains practical corrosion control solutions via design, proper materials selection, and implementation of good corrosion control engineering practices.

Shop the Latest ECS Titles at **wiley.com**

INTERESTED IN PUBLISHING WITH US?
Please contact **publications@electrochem.org** to discuss your idea.

WILEY

- CD5827